Appendix A-4
Sulfide Tailings

Appendix A-4

Bulk geotechnical samples of sulfide tailings were taken at several trench locations for field and laboratory testing of mechanical properties. Field tests included vane shear tests, nuclear density tests and laboratory tests performed gradations, plasticity indices, specific gravity, direct shear tests.

Sulfide Tails Testing		
Description	**Standard Reference**	**Tests**
Field Moisture/Density	ASTM D6938	12
Laboratory Moisture	ASTM D 2216	15
Plasticity Index	ASTM D 4318	15
Gradation	ASTM D 422	15
Moisture Density Relationship	ASTM D 1557	6
Soil Classification (USCS)	ASTM D 2487	15
Specific Gravity	ASTM D 5550	4
Direct Shear	ASTM D 3080	4
Flexible Wall Hydraulic Conductivity	ASTM D 5084	2

Sample ID	Description
SST	South Sulfide Tails Samples
NST	North Sulfide Tails
Clay Tails TP	North Sulfide Tails borrow pit
TP-On Ox	North VLT oxide tails data presented in chapter 5

Black Eagle Consulting, Inc. 1345 Capital Boulevard, Suite A Telephone: 775/359-6600 Email: mail@blackeagleconsulting.com
Geotechnical & Construction Services Reno, Nevada 89502-7140 Facsimile: 775/359-7766

Mr. Rich Mattucci
Brown and Caldwell
3264 Goni Road, Suite 153
Carson City, Nevada 89706

June 29, 2009
Project No.: 0155-21-1

RE: Summary of Site Sampling and Materials Testing – Yerington Mine Site
Yerington, Nevada

Dear Mr. Mattucci:

Black Eagle Consulting, Inc. is pleased to present the results of our site sampling and materials testing performed at the Yerington Mine site in Yerington, Nevada. All sampling and testing was performed in accordance with the scope of work outlined in the Brown and Caldwell Task Order #29 Authorization dated April 20, 2009.

Sulfide Tailings

Field Sampling and Testing

Sampling of the oxide tailings proposed for use as tailings capping material was performed in May 2009 by excavating 5 test pits, while sampling and field testing of the sulfide tailings was performed in May 2009 by excavating a total of 12 test pits in three locations: the south landfill area, the north landfill area, and the clay tailings area. The locations of the test pits are shown on the attached Plate 1 - Sampling Locations. Test pitting was accomplished using a John Deere® 160LC trackhoe to a depth of approximately 20 feet below existing grade. Bulk samples for index testing were collected from excavation spoils obtained at specific depths in each material horizon. Due to the depth of the test pit and associated safety concerns, the depth to changes in stratigraphy and total depth of excavation in the oxide tailings material could only be approximated.

During test pit excavation within the oxide tailings material, representative material excavated from the test pit was spread out in a single approximate 18-inch-thick loose lift adjacent to the test pit and subjected to approximately 4 passes by the trackhoe. This was performed three times: at the lower bench, the middle bench, and the upper bench in the existing oxide tailings stockpile area. Nuclear density testing was then performed on the completed pads.

A nuclear density gauge was used to determine the in situ moisture content and dry density of the material present at the ground surface at each test pit location in the sulfide tailings. Vane shear testing was also performed at the surface of each test pit in the sulfide tailings prior to excavation in order to document the in situ shear strength of the material.

A geologist examined and identified all soils in the field in accordance with American Society for Testing and Materials (ASTM) D 2488. During test pitting, representative bulk samples were placed in sealed plastic bags and returned to our Reno, Nevada, laboratory for possible testing. Additional soil classification was subsequently performed in accordance with ASTM 2487 (Unified Soil Classification System [USCS]) upon completion of laboratory testing as described below. Logs of the test pits are presented as Plate 2 - Test Pit Logs, and a USCS chart has been included as Plate 3 - Graphic Soils Classification Chart. Sulfide tailings test pits are denoted are denoted as SST, NST, and Clay Tails.

A summary of the sampling locations and field testing is presented in Table 1 – Oxide Tailings, Landfill and Clay Tailings Sampling Summary.

TABLE 1- OXIDE TAILINGS, LANDFILL AND CLAY TAILINGS SAMPLING SUMMARY

Test Location	Location Designation Test Pit (TP) Number	Test Depth (Inches)	Moisture Content (%)	Dry Density (pcf)	Vane Shear Value	Shear Strength (kPa)	Shear Strength (psi)	UTM Coordinates	
								Northings	Eastings
South Landfill Area	SST TP-01	6	5.7	91.3	96	145	21	4,319,809	309,684
	SST TP-02	6	6.4	93.5	80	121	18	4,319,877	309,785
	SST TP-03	6	11.4	84.3	93	141	20	4,319,984	309,670
North Landfill Area	NST TP-04	6	4.6	91.5	48	73	11	4,320,462	310,160
	NST TP-05	6	5.1	90.4	42	64	9	4,320,588	310,358
	NST TP-06	6	4.9	83.4	42	64	9	4,320,473	310,490
	NST TP-07	6	12.3	82.7	48	73	11	4,320,636	310,516
	NST TP-08	6	NT	NT	NT	NT	NT	4,320,677	310,171
Clay Tailings Area	Clay Tails TP-09	6	8.9	110.6	103	156	23	4,321,066	310,250
	Clay Tails TP-10	6	11.9	89.7	74	112	16	4,320,926	310,275
	Clay Tails TP-11	6	13.4	86.1	135	204	30	NR	NR
	Clay Tails TP-12	6	8.9	86.4	37	56	8	4,320,881	310,456
Lower Bench	TP-01 OX	6*	5.2	111.1	NT	NT	NT	4,320,056	308,481
		12*	5.2	113	NT	NT	NT		
	TP-02 OX	6*	7.1	98.5	NT	NT	NT	4,320,172	308,386
		12*	5.4	114.3	NT	NT	NT		
Middle Bench	TP-03 OX	6*	6.4	104.3	NT	NT	NT	4,319,981	308,410
		12*	5.6	109.5	NT	NT	NT		
Upper Bench	TP-04 OX	6*	5.2	113.6	NT	NT	NT	4,319,915	308,358
		12*	4.7	117.6	NT	NT	NT		
	TP-05 OX	6*	5.2	113.2	NT	NT	NT	4,320,072	308,289
		12*	4.9	115.9	NT	NT	NT		

NR = Not Recorded
NT = Not Tested
* Test performed on 18-inch section of oxide tailings material spread out and compacted by 4 passes of a John Deere® 160LC trackhoe.

Laboratory Testing

All soils testing performed in the Black Eagle Consulting, Inc. soils laboratory is conducted in accordance with the standards and methodologies described in Volume 4.08 of the ASTM standards. Oxide tailings samples are denoted as OX, while sulfide tailings samples are denoted as SST, NST, and Clay Tails.

Representative samples of the oxide and sulfide tailings were analyzed to determine their in situ moisture content (ASTM D 2216), grain size distribution (ASTM D 422), and plasticity index (ASTM D 4318). Test results were used to classify the soils according to ASTM D 2487 and to verify field logs, which were then updated as appropriate. Classification in this manner provides an indication of the soil's mechanical properties. Results of these tests are shown on Plate 4 - Index Test Results.

Moisture-density relationship tests (ASTM D 1557) were performed on representative samples of the oxide and sulfide tailings. The maximum density shown by this test is compared with field densities to determine the percent relative compaction. The moisture density curves are included as Plate 5 Moisture-Density Relationship Test Results.

Specific gravity tests (ASTM D 5550) were performed on representative samples of oxide and sulfide tailings to aid in hydrometer and direct shear testing of these materials. Test results are presented in Table 2 – Oxide and Sulfide Tailings Laboratory Test Summary.

Direct shear tests (ASTM D 3080) were also performed on representative samples of sulfide tailings. Tests were run on remolded, inundated samples under various normal loads in order to develop a Mohr's strength envelope. For remolded samples, the sample was screened to remove particles larger than the number 4 sieve prior to testing. Results of these tests are shown on Plate 6 - Direct Shear Test Results.

Hydraulic conductivity tests (ASTM D 5084) were performed on representative samples of sulfide tailings. The tests were performed on samples remolded to approximately 90 percent of the materials maximum dry density (ASTM D 1557) at optimum moisture content. A confining pressure of 5 pounds per square inch (psi) was used during testing. Results of these tests are shown on Plate 7 - Hydraulic Conductivity Test Results.

A summary of all the laboratory testing performed on the oxide and sulfide tailings is shown in Table 2.

TABLE 2 – OXIDE AND SULFIDE TAILINGS LABORATORY TEST SUMMARY

Sample Identification and Location Test Pit (TP) No.	Sample Depth (ft)	Sample Number	Liquid Limit (LL)	Plastic Limit (PL)	Plasticity Index (PI)	% < #200 Sieve	Maximum Size (mm)	Water Content (%)	Maximum Dry Density (pcf)	Optimum Moisture Content (%)	Specific Gravity	Angle of Internal Friction (Degrees)	Cohesion (psf)	Hydraulic Conductivity (cm/sec)	USCS Classification
SST TP-01	0.0	Bulk	NV	NP	NP	18	4.75	9.4	104.3	14.1	2.587	47	523		SM
SST TP-01	1.5	A	NV	NP	NP	13	4.75	8.3							SM
SST TP-02	0.0	Bulk	NV	NP	NP	61	9.5	13.9	107.8	16.7	2.631	41	0	2.3×10^{-4}	ML
SST TP-02	1.5	A	NV	NP	NP	31	19	12.1							SM
SST TP-03	1.5	A	NV	NP	NP	67	9.5	14.0							ML
NST TP-04	1.5	A	NV	NP	NP	12	19	3.6							SM
NST TP-05	0.0	Bulk	NV	NP	NP	64	19	19.5	111.3	12.0	2.601	41	120		ML
NST TP-06	0.0	Comp	NV	NP	NP	67	19	18.7	117.5	13.0	2.610	41	149	8.9×10^{-5}	ML
NST TP-07	1.5	A	NV	NP	NP	61	2	16.0							ML
NST TP-08	15.0	B	NV	NP	NP	92	12.5	26.9							ML
Clay Tails TP-09	2.0	A	NV	NP	NP	33	25	8.7							SM
Clay Tails TP-10	2.0	A	25	23	1	97	0.425	21.1							ML
Clay Tails TP-11	0.0	Bulk	NV	NP	NP	92	12.5	15.3	105.2	14.4					ML
Clay Tails TP-11	2.0	A	24	22	2	90	4.75	12.5							ML
Clay Tails TP-12	0.0	Bulk	NV	NP	NP	94	2	14.4	103.9	14.1					ML
TP-01 OX	0.0	Bulk	27	20	7	9	19	5.7	135.0	5.9	2.587				SP-SC
TP-01 OX	5.0	A	28	16	12	8	19	5.2							SP-SC
TP-02 OX	20.0	D	29	18	11	9	19	6.5			2.667				GP-GC
TP-03 OX	0.0	Bulk	28	19	9	11	19	6.4	136.2	5.1	2.636				SP-SC
TP-03 OX	10.0	B	31	18	13	10	19	6.8							SP-SC
TP-04 OX	15.0	C	28	20	8	9	19	7.1							GP-GC
TP-05 OX	0.0	Bulk	27	20	7	12	19	6.4	136.8	5.4	2.643				SP-SC

NV = No Value
NP = Non-Plastic

Seismic Design Criteria

The 2006 *International Building Code* (ICC, 2006), adopted by the City of Yerington, requires a detailed soils evaluation to a depth of 100 feet to develop appropriate soils criteria. However, the code states that a Site Class D may be used as a default value when the soil properties are not known in sufficient detail to determine the soil profile type. The Site Class D soil profile is for stiff soils with a shear velocity between 600 and 1,200 feet per second, or with an N (Standard Penetration Test [SPT]) value between 15 and 50 or an undrained shear strength between 1,000 and 2,000 pounds per square foot (psf). Based on our experience and the geology at the Yerington mine site, it is our opinion that the default Site Class D is appropriate. With that assumption, the recommended seismic design criteria follow:

TABLE 3 - SEISMIC DESIGN CRITERIA USING 2006 *INTERNATIONAL BUILDING CODE* (USGS, 2007)	
Approximate Latitude	39.00
Approximate Longitude	-119.20
Spectral Response at Short Periods, S_s, percent of gravity	1.246
Spectral Response at 1-Second Period, S_1, percent of gravity	0.478
Site Class	D
Site Coefficient F_a, decimal	1.00
Site Coefficient F_v, decimal	1.32
Site Adjusted Spectral Response at Short Periods, S_{MS}, percent of gravity	1.246
Site Adjusted Spectral Response at Long Periods, S_{M1}, percent of gravity	0.632

Closing

This report has been prepared with generally accepted geotechnical practices. The information submitted is based upon field exploration performed at the locations described in this letter-report. This report does not reflect soils or ground water variations that may be evident during the construction period. We recommend our firm be retained to perform construction observation in all phases of the project related to geotechnical factors. The owner shall be responsible for distribution of this geotechnical investigation to all designer and contractors whose work is related to geotechnical factors.

We appreciate being of service to you on this project. If you have any questions, or require additional information or clarification, please do not hesitate to contact us.

Sincerely,

Black Eagle Consulting, Inc.

Patrick A. Pilling, Ph.D., P.E.
President

PAP:mrc/lmk

Enclosures: Plate 1 – Sampling Locations
Plate 2 – Test Pit Logs
Plate 3 – Graphic Soils Classification Chart
Plate 4 – Index Test Results
Plate 5 – Moisture-Density Relationship Test Results
Plate 6 – Direct Shear Test Results
Plate 7 – Hydraulic Conductivity Test Results

Copies to: Addressee (3 copies)

References:

American Society for Testing and Materials (ASTM), 2005, *Soil and Rock; Dimension Stone; Geosynthetics,* Volume 4.08.

International Code Council (ICC), 2006, *International Building Code.*

United States Geological Survey (USGS), 2007, *Earthquake Ground Motion Parameters,* Version 5.0.8.

ENCLOSURES

Black Eagle Consulting, Inc.
Geotechnical & Construction Services
1345 Capital Boulevard, Suite A
Reno, Nevada 89502-7140
Telephone: 775/359-6600
Facsimile: 775/359-7766

Brown & Caldwell

Sample Locations

Yerington Mine

Yerington, Nevada

Project No.
0155-21-1

Plate 1

TEST PIT LOG

TEST PIT NO.: SST TP-01 | DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC | DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM | GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					0	GP-GC		0.0' - 1.2': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
A	GRAB		8.3	NP	2			1.2' - 18.0': **Silty Sand** Tan, yellow, dry, loose to medium dense, with 13% non-plastic fines, and 87% fine to coarse sand.
					4			
B	GRAB				6			
					8			
					10	SM		Occasional thin gray clay layers up to 3 inches thick.
C	GRAB				12			
					14			
D	GRAB				16			
					18	ML		18.0' - 20.0': **Sandy Silt** Gray, slightly moist, very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to coarse sand.
E	GRAB							

Excavated in the South Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell
Yerington Mine
Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

TEST PIT LOG

TEST PIT NO.: SST TP-02 | DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC | DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM | GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
						GP-GC		0.0' - 0.8': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
						ML		0.8' - 1.4': **Sandy Silt** Gray, slightly moist, very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to coarse sand.
A	GRAB		12.1	NP	2			1.4' - 9.0': **Silty Sand** Yellow brown, slightly moist, loose to medium dense, with 13% non-plastic fines, and 87% fine to coarse sand.
					4			
B	GRAB					SM		
					6			
					8			
					10			9.0' - 13.0': **Sandy Silt** Gray, yellow brown, slightly moist, stiff to very stiff, with an estimated 70-75% non-plastic fines, and 25-30% fine to coarse sand.
C	GRAB					ML		
					12			
					14			13.0' - 17.5': **Sandy Silt** Blue-gray, yellow brown, slightly moist, very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to coarse sand.
D	GRAB					ML		
					16			
					18			17.5' - 20.0': **Silt** Dark gray, slightly moist, stiff to very stiff, with an estimated 90-95% non-plastic fines, and 5-10% fine to coarse sand.
E	GRAB					ML		

Excavated in the South Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

TEST PIT LOG

TEST PIT NO.: SST TP-03 DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
						GP-GC		0.0' - 1.0': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
A	GRAB		14.0	NP	2	ML		1.0' - 4.0': **Sandy Silt** Reddish brown, gray, thinly bedded, slightly moist, stiff, with 67% non-plastic fines, and 33% fine to coarse sand.
					4			4.0' - 9.0': **Sandy Silt** Yellow brown, gray, slightly moist, stiff to very stiff, with an estimated 70-75% non-plastic fines, and 25-30% fine to coarse sand.
B	GRAB				6	ML		
					8			
					10			9.0' - 13.0': **Sandy Silt** Gray, slightly moist, very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to coarse sand.
C	GRAB					ML		
					12			
					14			13.0' - 17.0': **Sandy Silt** Blue-gray, slightly moist, stiff to very stiff, with an estimated 70-75% non-plastic fines, and 25-30% fine to coarse sand.
D	GRAB					ML		
					16			
					18			17.0' - 20.0': **Silt** Dark gray, slightly moist, stiff to very stiff, with an estimated 90-95% non-plastic fines, and 5-10% fine to coarse sand.
						ML		
E	GRAB							

Excavated in the South Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell
Yerington Mine
Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: NST TP-04 | DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC | DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM | GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
A	GRAB		3.6	NP	2	GP-GC		0.0' - 4.0': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
					4	SM		4.0' - 5.0': **Silty Sand** Gray, dry to slightly moist, medium dense, with 12% non-plastic fines, 85% fine to coarse sand, and 3% fine to coarse angular gravel.
B	GRAB				6	SM		5.0' - 8.0': **Silty Sand** Yellow brown, blue-gray, slightly moist, medium dense, with an estimated 15-20% non-plastic fines, and 80-85% fine to coarse sand.
					8			8.0' - 14.0': **Sandy Silt** Yellow brown, gray, slightly moist, firm to stiff, with an estimated 60-65% non-plastic fines, and 35-40% fine to coarse sand.
C	GRAB				10	ML		
					12			
					14			14.0' - 17.0': **Sandy Silt** Gray, slightly moist, stiff, with an estimated 60-65% non-plastic fines, and 35-40% fine to coarse sand.
D	GRAB				16	ML		
					18	ML		17.0' - 20.0': **Silt** Dark gray, slightly moist, stiff, with an estimated 90-95% non-plastic fines, and 5-10% fine to coarse sand.
E	GRAB							

Excavated in the North Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell
Yerington Mine
Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: NST TP-05

DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					0	GP-GC		0.0' - 6.0': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
A	GRAB				6	SM		6.0' - 8.0': **Silty Sand** Blue-gray, slightly moist, medium dense, with an estimated 15-20% non-plastic fines, and 80-85% fine to coarse sand.
B	GRAB				8	ML		8.0' - 20.0': **Silt** Blue-gray, slightly moist, stiff, with an estimated 90-95% non-plastic fines, and 5-10% fine to coarse sand.
C	GRAB				14			
D	GRAB				18			

Excavated in the North Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: NST TP-06 | DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC | DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM | GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2	GP-GC		0.0' - 4.0': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
					4	SM		4.0' - 6.0': **Silty Sand** Blue-gray, slightly moist, medium dense, with an estimated 15-20% non-plastic fines, and 80-85% fine to coarse sand.
A	GRAB				6			
					8	ML		6.0' - 13.0': **Sandy Silt** Dark gray, slightly moist, stiff to very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to coarse sand.
B	GRAB				10			
					12			
					14	ML		13.0' - 20.0': **Sandy Silt** Blue-gray, slightly moist, stiff to very stiff, with an estimated 65-70% non-plastic fines, and 30-35% fine to medium sand.
C	GRAB				16			
					18			
D	GRAB							

Excavated in the North Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell
Yerington Mine
Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: NST TP-07

DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2	GP-GC		0.0' - 8.0': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
					4			
					6			
					8			
A	GRAB					ML		8.0' - 9.5': **Sandy Silt** Gray, slightly moist, stiff to very stiff, with 60-65% non-plastic fines, and 35-40% fine to coarse sand.
B	GRAB				10			9.5' - 20.0': **Silt** Dark gray, slightly moist, stiff to very stiff, with an estimated 90-95% non-plastic fines, and 5-10% fine to coarse sand.
					12			
					14	ML		
C	GRAB				16			
					18			
D	GRAB							

Excavated in the North Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: NST TP-08

DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2	GP-GC		0.0' - 8.5': **Poorly Graded Gravel with Clay and Sand** Tan, yellow, dry, dense to very dense, with an estimated 5-10% low to medium plasticity fines, 15-20% fine to coarse sand, and 70-75% fine to coarse angular to subangular gravel. Cap for tailings.
					4			
					6			
					8			
A	GRAB				10	ML		8.5' - 12.0': **Sandy Silt** Light gray, slightly moist, stiff to very stiff, with an estimated 70-75% non-plastic fines, and 25-30% fine to coarse sand.
					12			12.0' - 20.0': **Silt** Blue-gray, slightly moist, stiff to very stiff, with 90-95% non-plastic fines, and 5-10% fine to coarse sand.
B	GRAB		26.9	NP	14			
					16	ML		
					18			
C	GRAB							

Excavated in the North Sulfide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: 0155-21-1

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: Clay Tails TP-09

DATE: 5/29/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
A	GRAB		8.7	NP	2–4	SM		0.0' - 5.0': **Silty Sand** Gray, dry, medium dense, with 30-35% non-plastic fines, 60-70% fine to coarse sand, and <5% fine to coarse subangular to subrounded gravel. Native soil encountered at 5 feet bgs.
B	GRAB				6			
					8			
					10			
					12			
					14			
					16			
					18			

Excavated in the Clay Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

TEST PIT LOG

TEST PIT NO.: Clay Tails TP-10 | DATE: 5/30/2009

TYPE OF HOE: John Deere 160C LC | DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM | GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
								0.0' - 15.0': **Silt** Gray, dry to slightly moist, firm to stiff, with >95% non-plastic to low plasticity fines, and <5% fine to medium sand.
A	GRAB				2			
					4			
B	GRAB		21.1	2	6			
					8	ML		
C	GRAB				10			
					12			
					14			
D	GRAB				16			15.0' - 20.0': **Silt** Dark gray, slightly moist, stiff, with an estimated 90-95% non-plastic to low plasticity fines, and 5-10% fine to medium sand.
					18	ML		
E	GRAB							

Excavated in the Clay Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: Clay Tails TP-11 DATE: 5/30/2009

TYPE OF HOE: John Deere 160C LC DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2			0.0' - 5.0': **Silt** Gray to reddish brown, dry to slightly moist, stiff, with 90-95% non-plastic fines, 5-10% fine to coarse sand, and a trace of fine angular gravel.
B	GRAB		12.5	2	4	ML		
C	GRAB				6			5.0' - 20.0': **Silt** Gray, dark gray, slightly moist, stiff, with an estimated 90-95% non-plastic to low plasticity fines, and 5-10% fine to medium sand.
D	GRAB				10			
					12	ML		
E	GRAB				14			
					16			
F	GRAB				18			

Excavated in the Clay Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: Clay Tails TP-12 DATE: 5/30/2009

TYPE OF HOE: John Deere 160C LC DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					0			0.0' - 15.0': **Silt** Gray to reddish brown, dry to slightly moist, stiff, with 90-95% non-plastic fines, and 5-10% fine to medium sand.
A	GRAB				2			
					4			
B	GRAB				6			
					8	ML		
C	GRAB				10			
					12			
					14			
D	GRAB				16			15.0' - 20.0': **Silt** Gray, dark gray, slightly moist, stiff, with an estimated 90-95% non-plastic to low plasticity fines, and 5-10% fine to medium sand.
					18	ML		
E	GRAB							

Excavated in the Clay Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell
Yerington Mine
Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

TEST PIT LOG

TEST PIT NO.: TP-01 OX

DATE: 5/27/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2	SP-SC		0.0' - 5.0': **Poorly Graded Sand with Clay and Gravel** Brown, tan, dry to slightly moist, dense, with an estimated 10-15% non-plastic to low plasticity fines, 45-50% fine to coarse sand, and 35-40% fine to coarse angular gravel.
					4			
A	GRAB		5.2	12	6			5.0' - 20.0': **Poorly Graded Sand with Clay and Gravel** Brown, dark brown, slightly moist, very dense, with 5-10% medium plasticity fines, 45-50% fine to coarse sand, and 40-45% fine to coarse angular gravel.
					8			
B	GRAB				10			
					12	SP-SC		
					14			
C	GRAB				16			
					18			
D	GRAB							

Excavated in the Oxide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: TP-02 OX

DATE: 5/27/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					2	SP-SC		0.0' - 5.0': **Poorly Graded Sand with Clay and Gravel** Brown, tan, dry to slightly moist, dense, with an estimated 10-15% non-plastic to low plasticity fines, 45-50% fine to coarse sand, and 35-40% fine to coarse angular gravel.
					4			
A	GRAB				6			5.0' - 15.0': **Poorly Graded Sand with Clay and Gravel** Brown, dark brown, slightly moist, very dense, with an estimated 5-10% medium plasticity fines, 45-50% fine to coarse sand, and 40-45% fine to coarse angular gravel.
					8			
B	GRAB				10	SP-SC		
					12			
					14			
C	GRAB				16			15.0' - 20.0': **Poorly Graded Gravel with Clay and Sand** Brown, slightly moist, very dense, with 5-10% medium plasticity fines, 30-35% fine to coarse sand, and 55-60% angular gravel.
					18	GP-GC		
D	GRAB		6.5	11				

Excavated in the Oxide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

TEST PIT LOG

TEST PIT NO.: TP-03 OX

DATE: 5/28/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
A	GRAB				2, 4, 6			0.0' - 20.0': **Poorly Graded Sand with Clay and Gravel** Brown, dark brown, slightly moist, very dense, with an estimated 5-15% medium plasticity fines, 40-50% fine to coarse sand, and 35-45% fine to coarse angular gravel.
B	GRAB		6.8	13	8, 10	SP-SC		
C	GRAB				12, 14, 16			
D	GRAB				18			

Excavated in the Oxide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: TP-04 OX

DATE: 5/28/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					0			0.0' - 12.0': **Poorly Graded Sand with Clay and Gravel** Brown, dark brown, slightly moist, very dense, with an estimated 5-15% medium plasticity fines, 40-50% fine to coarse sand, and 35-45% fine to coarse angular gravel.
					2			
					4			
A	GRAB				6	SP-SC		
					8			
B	GRAB				10			
					12			12.0' - 20.0': **Poorly Graded Gravel with Clay and Sand** Brown, slightly moist, very dense, with 5-10% medium plasticity fines, 40-45% fine to coarse sand, and 45-50% angular gravel.
					14			
C	GRAB		7.1	8				
					16	GP-GC		
					18			
D	GRAB							

Excavated in the Oxide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

TEST PIT LOG

TEST PIT NO.: TP-05 OX

DATE: 5/28/2009

TYPE OF HOE: John Deere 160C LC

DEPTH TO GROUND WATER (ft): NE

LOGGED BY: SMM

GROUND ELEVATION (ft): NA

SAMPLE NO.	SAMPLE TYPE	PENETROMETER (tsf)	MOISTURE (%)	PLASTICITY INDEX	DEPTH (ft)	USCS SYMBOL	LITHOLOGY	DESCRIPTION
					0			0.0' - 15.0': **Poorly Graded Sand with Clay and Gravel** Brown, dark brown, slightly moist, very dense, with an estimated 5-15% medium plasticity fines, 40-50% fine to coarse sand, and 35-45% fine to coarse angular gravel.
					2			
					4			
A	GRAB				6			
					8	SP-SC		
B	GRAB				10			
					12			
					14			
C	GRAB				16			15.0' - 20.0': **Poorly Graded Gravel with Clay and Sand** Brown, slightly moist, very dense, with 5-10% medium plasticity fines, 40-45% fine to coarse sand, and 45-50% angular gravel.
					18	GP-GC		
D	GRAB							

Excavated in the Oxide Tailings.

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
(775) 359-6600

Brown & Caldwell

Yerington Mine

Yerington, NV

PROJECT NO.: **0155-21-1**

PLATE: 2

SHEET 1 OF 1

BORING_LOG 0155211.GPJ BLKEAGLE.GDT 6/19/2009

SOIL CLASSIFICATION CHART

MAJOR DIVISIONS			SYMBOLS GRAPH	SYMBOLS LETTER	TYPICAL DESCRIPTIONS
COARSE GRAINED SOILS	GRAVEL AND GRAVELLY SOILS	CLEAN GRAVELS (LITTLE OR NO FINES)		GW	WELL-GRADED GRAVELS, GRAVEL - SAND MIXTURES, LITTLE OR NO FINES
				GP	POORLY-GRADED GRAVELS, GRAVEL - SAND MIXTURES, LITTLE OR NO FINES
	MORE THAN 50% OF COARSE FRACTION RETAINED ON NO. 4 SIEVE	GRAVELS WITH FINES (APPRECIABLE AMOUNT OF FINES)		GM	SILTY GRAVELS, GRAVEL - SAND - SILT MIXTURES
				GC	CLAYEY GRAVELS, GRAVEL - SAND - CLAY MIXTURES
MORE THAN 50% OF MATERIAL IS LARGER THAN NO. 200 SIEVE SIZE	SAND AND SANDY SOILS	CLEAN SANDS (LITTLE OR NO FINES)		SW	WELL-GRADED SANDS, GRAVELLY SANDS, LITTLE OR NO FINES
				SP	POORLY-GRADED SANDS, GRAVELLY SAND, LITTLE OR NO FINES
	MORE THAN 50% OF COARSE FRACTION PASSING ON NO. 4 SIEVE	SANDS WITH FINES (APPRECIABLE AMOUNT OF FINES)		SM	SILTY SANDS, SAND - SILT MIXTURES
				SC	CLAYEY SANDS, SAND - CLAY MIXTURES
FINE GRAINED SOILS	SILTS AND CLAYS	LIQUID LIMIT LESS THAN 50		ML	INORGANIC SILTS AND VERY FINE SANDS, ROCK FLOUR, SILTY OR CLAYEY FINE SANDS OR CLAYEY SILTS WITH SLIGHT PLASTICITY
				CL	INORGANIC CLAYS OF LOW TO MEDIUM PLASTICITY, GRAVELLY CLAYS, SANDY CLAYS, SILTY CLAYS, LEAN CLAYS
				OL	ORGANIC SILTS AND ORGANIC SILTY CLAYS OF LOW PLASTICITY
MORE THAN 50% OF MATERIAL IS SMALLER THAN NO. 200 SIEVE SIZE	SILTS AND CLAYS	LIQUID LIMIT GREATER THAN 50		MH	INORGANIC SILTS, MICACEOUS OR DIATOMACEOUS FINE SAND OR SILTY SOILS
				CH	INORGANIC CLAYS OF HIGH PLASTICITY
				OH	ORGANIC CLAYS OF MEDIUM TO HIGH PLASTICITY, ORGANIC SILTS
HIGHLY ORGANIC SOILS				PT	PEAT, HUMUS, SWAMP SOILS WITH HIGH ORGANIC CONTENTS
FILL MATERIAL				--	FILL MATERIAL, NON-NATIVE

NOTE: DUAL SYMBOLS ARE USED TO INDICATE BORDERLINE SOIL CLASSIFICATIONS.

EXPLORATION SAMPLE TERMINOLOGY

Sample Type	Sample Symbol	Sample Code
Auger Cuttings		Auger
Bulk (Grab) Sample		Grab
Modified California Sampler		MC
Shelby Tube		SH or ST
Standard Penetration Test		SPT
Split Spoon		SS
No Sample		

GRAIN SIZE TERMINOLOGY

Component of Sample	Size Range
Boulders	Over 12 in. (300mm)
Cobbles	12 in. to 3 in. (300mm to 75mm)
Gravel	3 in. to #4 sieve (75mm to 2mm)
Sand	# 4 to #200 sieve (2mm to 0.074mm)
Silt or Clay	Passing #200 sieve (0.074mm)

RELATIVE DENSITY OF GRANULAR SOILS

N - Blows/ft	Relative Density
0 - 4	Very Loose
5 - 10	Loose
11 - 30	Medium Dense
31 - 50	Dense
greater than 50	Very Dense

PLASTICITY CHART

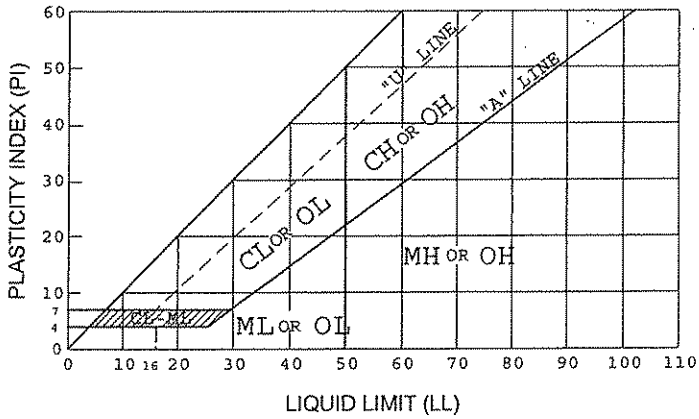

FOR CLASSIFICATION OF FINE-GRAINED SOILS AND FINE-GRAINED FRACTION OF COARSE-GRAINED SOILS

CONSISTENCY OF COHESIVE SOILS

Unconfined Compressive Strength, psf	N - Blows/ft	Consistency
less than 500	0 - 1	Very Soft
500 - 1,000	2 - 4	Soft
1,000 - 2,000	5 - 8	Firm
2,000 - 4,000	9 - 15	Stiff
4,000 - 8,000	16 - 30	Very Stiff
8,000 - 16,000	31 - 60	Hard
greater than 16,000	greater than 60	Very Hard

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

USCS Soil Classification Chart

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 3

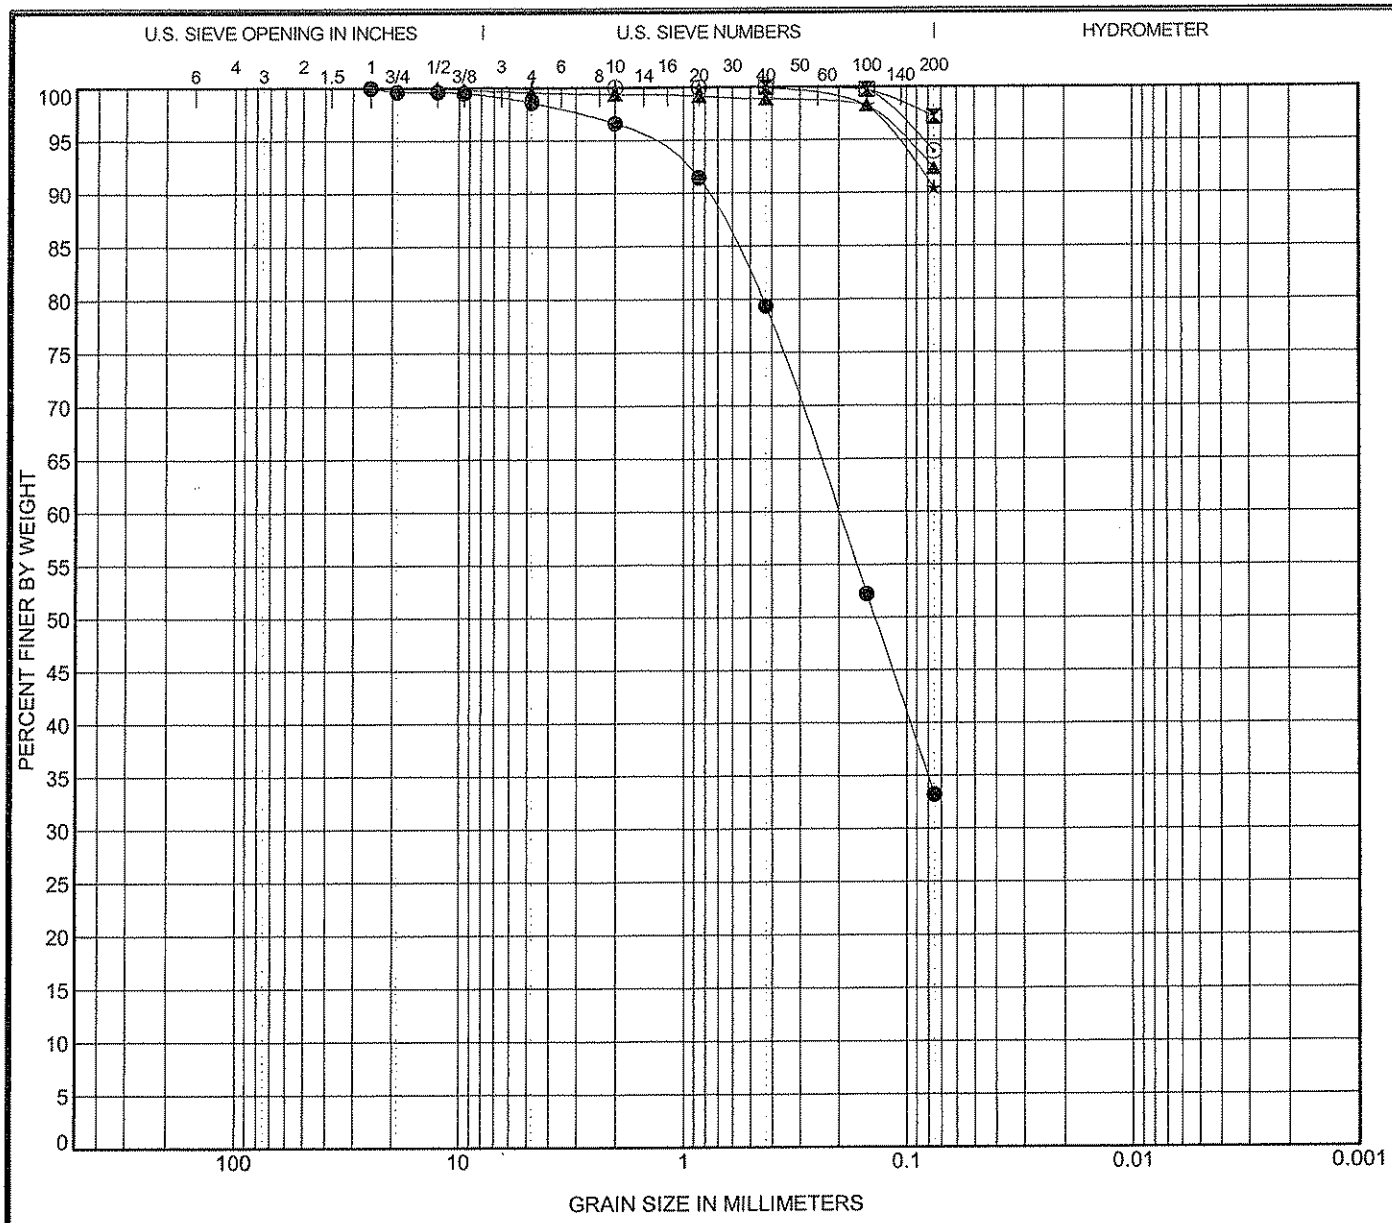

COBBLES	GRAVEL		SAND			SILT OR CLAY
	coarse	fine	coarse	medium	fine	

	Specimen Identification		USCS Classification	LL	PL	PI	Cc	Cu
●	**Clay Tails TP-09**	**2.0'**	**SILTY SAND (SM)**	**NP**	**NP**	**NP**		
⊠	**Clay Tails TP-10**	**2.0'**	**SILT (ML)**	**25**	**23**	**2**		
▲	**Clay Tails TP-11**	**0.0'**	**SILT (ML)**	**NP**	**NP**	**NP**		
★	**Clay Tails TP-11**	**2.0'**	**SILT (ML)**	**24**	**22**	**2**		
⊙	**Clay Tails TP-12**	**0.0'**	**SILT (ML)**	**NP**	**NP**	**NP**		

	Specimen Identification		D100	D60	D30	D10	MC %	%Gravel	%Sand	%Silt	%Clay
●	**Clay Tails TP-09**	**2.0'**	**25**	**0.202**			**8.7**	**1.4**	**65.4**	**33.2**	
⊠	**Clay Tails TP-10**	**2.0'**	**0.425**				**21.1**	**0.0**	**2.8**	**97.2**	
▲	**Clay Tails TP-11**	**0.0'**	**12.5**				**15.3**	**0.4**	**7.3**	**92.3**	
★	**Clay Tails TP-11**	**2.0'**	**4.75**				**12.5**	**0.0**	**9.6**	**90.4**	
⊙	**Clay Tails TP-12**	**0.0'**	**2**				**14.4**	**0.0**	**6.1**	**93.9**	

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

GRAIN SIZE DISTRIBUTION

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 4a

US GRAIN SIZE2 0155221.GPJ US_LAB.GDT 6/29/2009

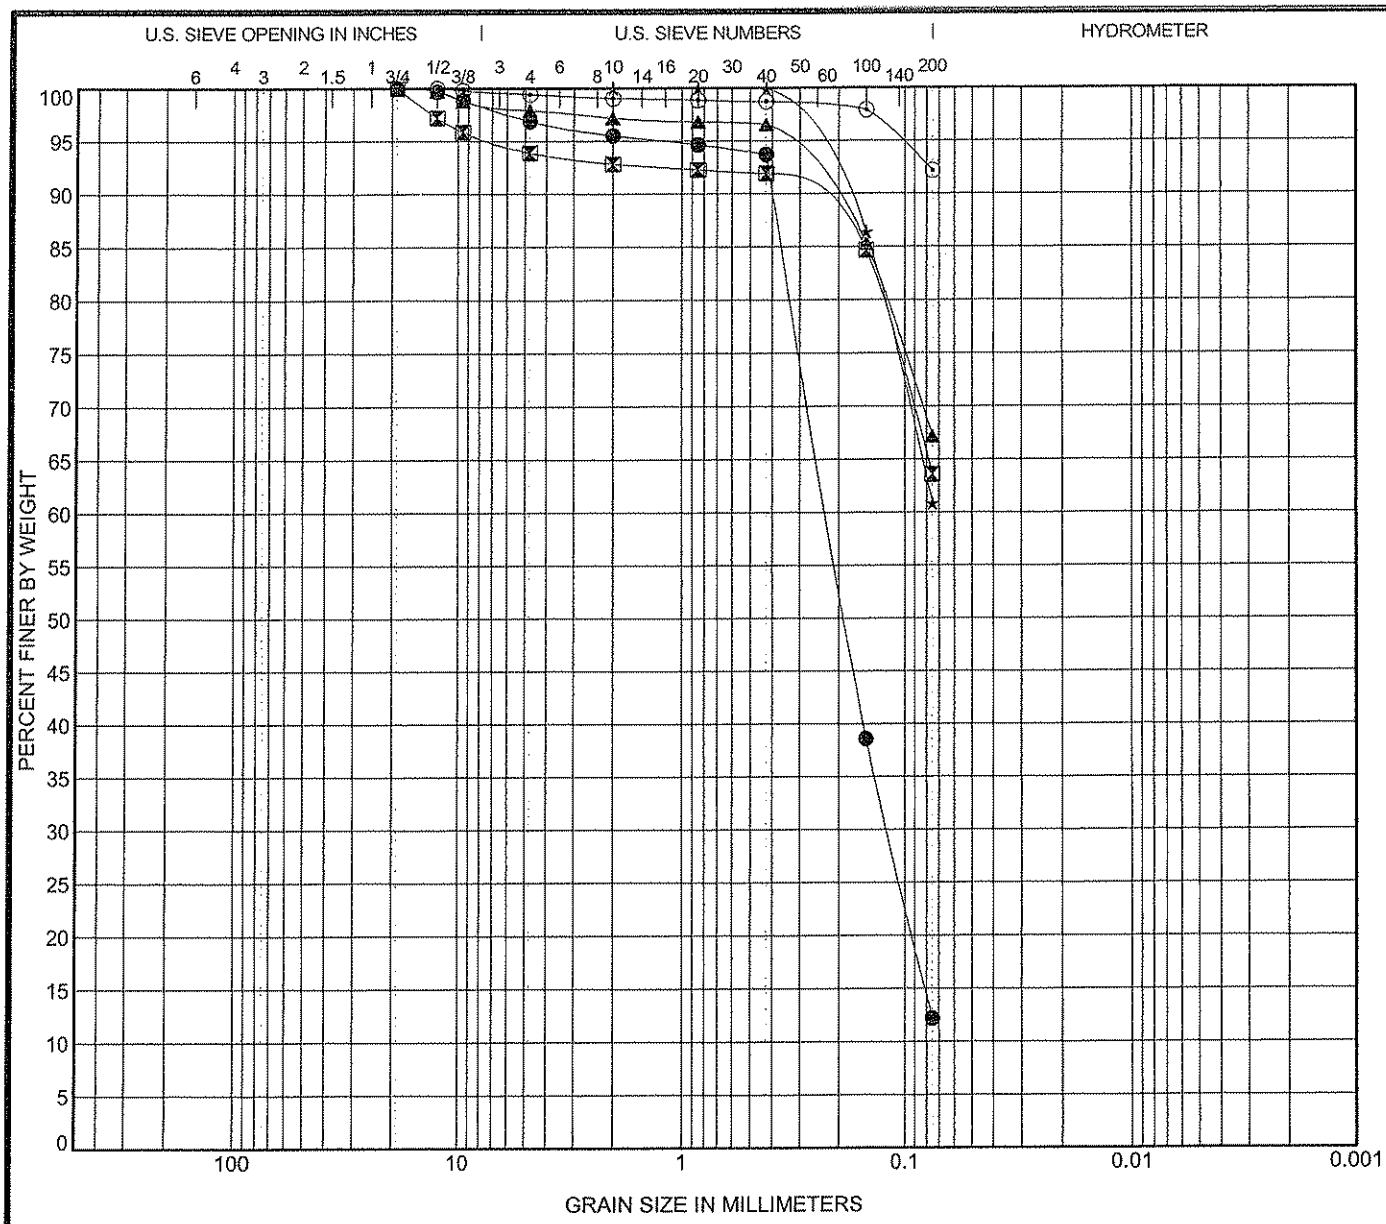

COBBLES	GRAVEL		SAND			SILT OR CLAY
	coarse	fine	coarse	medium	fine	

Specimen Identification		USCS Classification	LL	PL	PI	Cc	Cu
● NST TP-04	1.5'	SILTY SAND (SM)	NP	NP	NP	0.90	3.17
⊠ NST TP-05	0.0'	SANDY SILT (ML)	NP	NP	NP		
▲ NST TP-06	0.0'	SANDY SILT (ML)	NP	NP	NP		
★ NST TP-07	1.5'	SANDY SILT (ML)	NP	NP	NP		
⊙ NST TP-08	15.0'	SILT (ML)	NP	NP	NP		

Specimen Identification		D100	D60	D30	D10	MC %	%Gravel	%Sand	%Silt	%Clay
● NST TP-04	1.5'	19	0.225	0.12		3.6	3.1	84.7	12.2	
⊠ NST TP-05	0.0'	19				19.5	6.1	30.3	63.6	
▲ NST TP-06	0.0'	19				18.7	2.1	30.7	67.2	
★ NST TP-07	1.5'	2				16.0	0.0	39.2	60.8	
⊙ NST TP-08	15.0'	12.5				26.9	0.6	7.3	92.1	

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

GRAIN SIZE DISTRIBUTION

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 4b

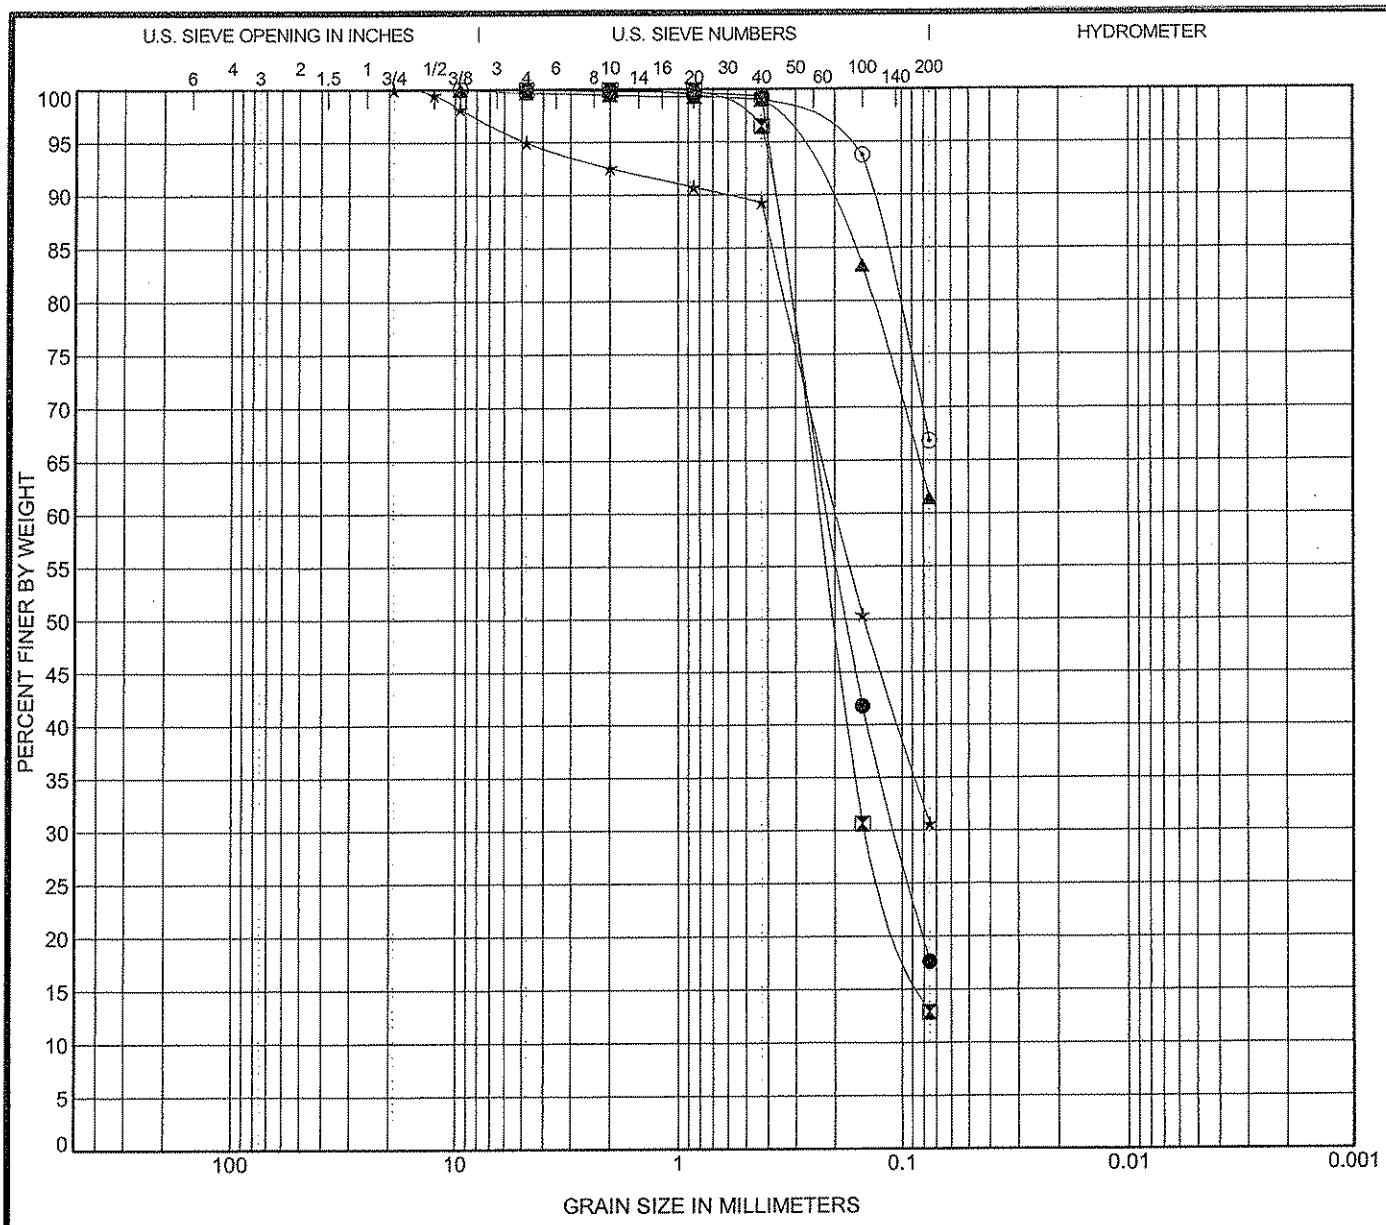

COBBLES	GRAVEL		SAND			SILT OR CLAY
	coarse	fine	coarse	medium	fine	

	Specimen Identification		USCS Classification	LL	PL	PI	Cc	Cu
●	SST TP-01	0.0'	SILTY SAND (SM)	NP	NP	NP		
⊠	SST TP-01	1.5'	SILTY SAND (SM)	NP	NP	NP		
▲	SST TP-02	0.0'	SANDY SILT (ML)	NP	NP	NP		
★	SST TP-02	1.5'	SILTY SAND (SM)	NP	NP	NP		
⊙	SST TP-03	1.5'	SANDY SILT (ML)	NP	NP	NP		

	Specimen Identification		D100	D60	D30	D10	MC %	%Gravel	%Sand	%Silt	%Clay
●	SST TP-01	0.0'	4.75	0.209	0.107		9.4	0.0	82.4	17.6	
⊠	SST TP-01	1.5'	4.75	0.239	0.146		8.3	0.0	87.1	12.9	
▲	SST TP-02	0.0'	9.5				13.9	0.3	38.2	61.4	
★	SST TP-02	1.5'	19	0.194			12.1	5.0	64.4	30.6	
⊙	SST TP-03	1.5'	9.5				14.0	0.0	33.1	66.8	

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

GRAIN SIZE DISTRIBUTION

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 4c

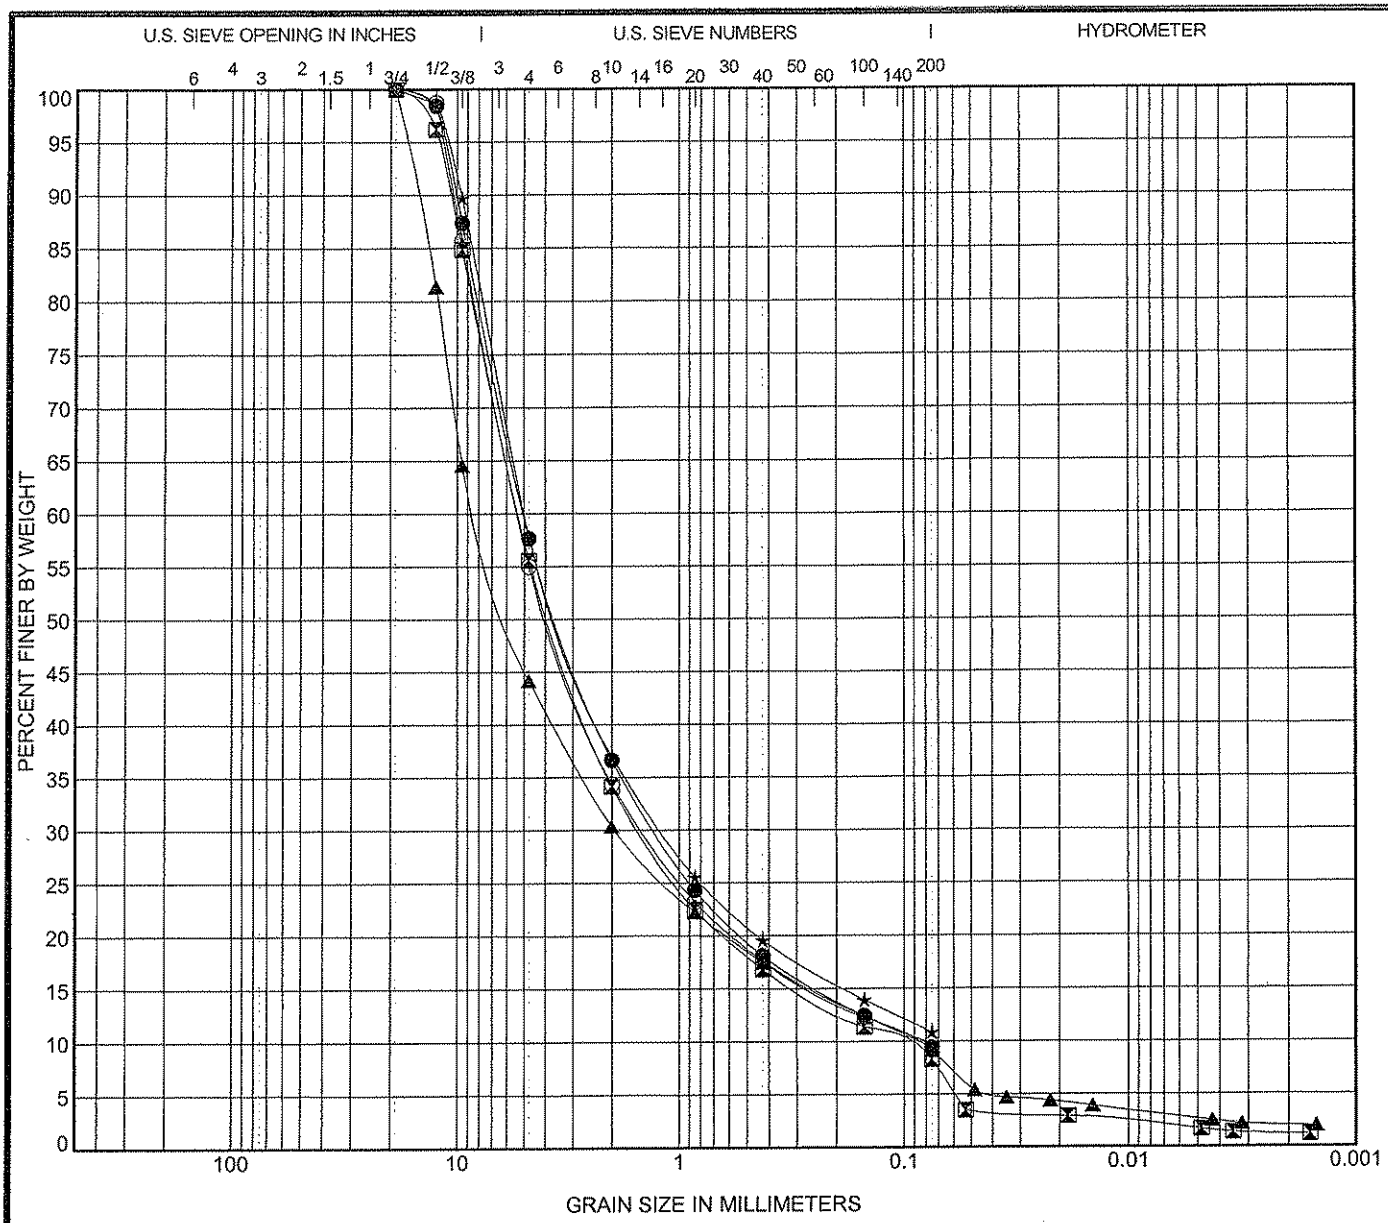

COBBLES	GRAVEL		SAND			SILT OR CLAY
	coarse	fine	coarse	medium	fine	

	Specimen Identification		USCS Classification	LL	PL	PI	Cc	Cu
●	TP-01 OX	0.0'	POORLY GRADED SAND with SILTY CLAY and GRAVEL (SP-SC)	27	20	7	3.70	58.51
⊠	TP-01 OX	5.0'	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)	28	16	12	3.79	48.17
▲	TP-02 OX	20.0'	POORLY GRADED GRAVEL with CLAY and SAND (GP-GC)	29	18	11	5.07	89.55
★	TP-03 OX	0.0'	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)	28	19	9	4.58	80.83
⊙	TP-03 OX	10.0'	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)	31	18	13	4.81	66.47

	Specimen Identification		D100	D60	D30	D10	MC %	%Gravel	%Sand	%Silt	%Clay
●	TP-01 OX	0.0'	19	5.017	1.262	0.086	5.7	42.3	48.2	9.4	
⊠	TP-01 OX	5.0'	19	5.273	1.479	0.109	5.2	44.4	47.3	6.6	1.7
▲	TP-02 OX	20.0'	19	8.13	1.934	0.091	6.5	55.8	35.0	6.5	2.7
★	TP-03 OX	0.0'	19	4.981	1.186		6.4	42.2	46.9	10.9	
⊙	TP-03 OX	10.0'	19	5.318	1.431	0.08	6.8	45.0	45.2	9.8	

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

GRAIN SIZE DISTRIBUTION

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 4d

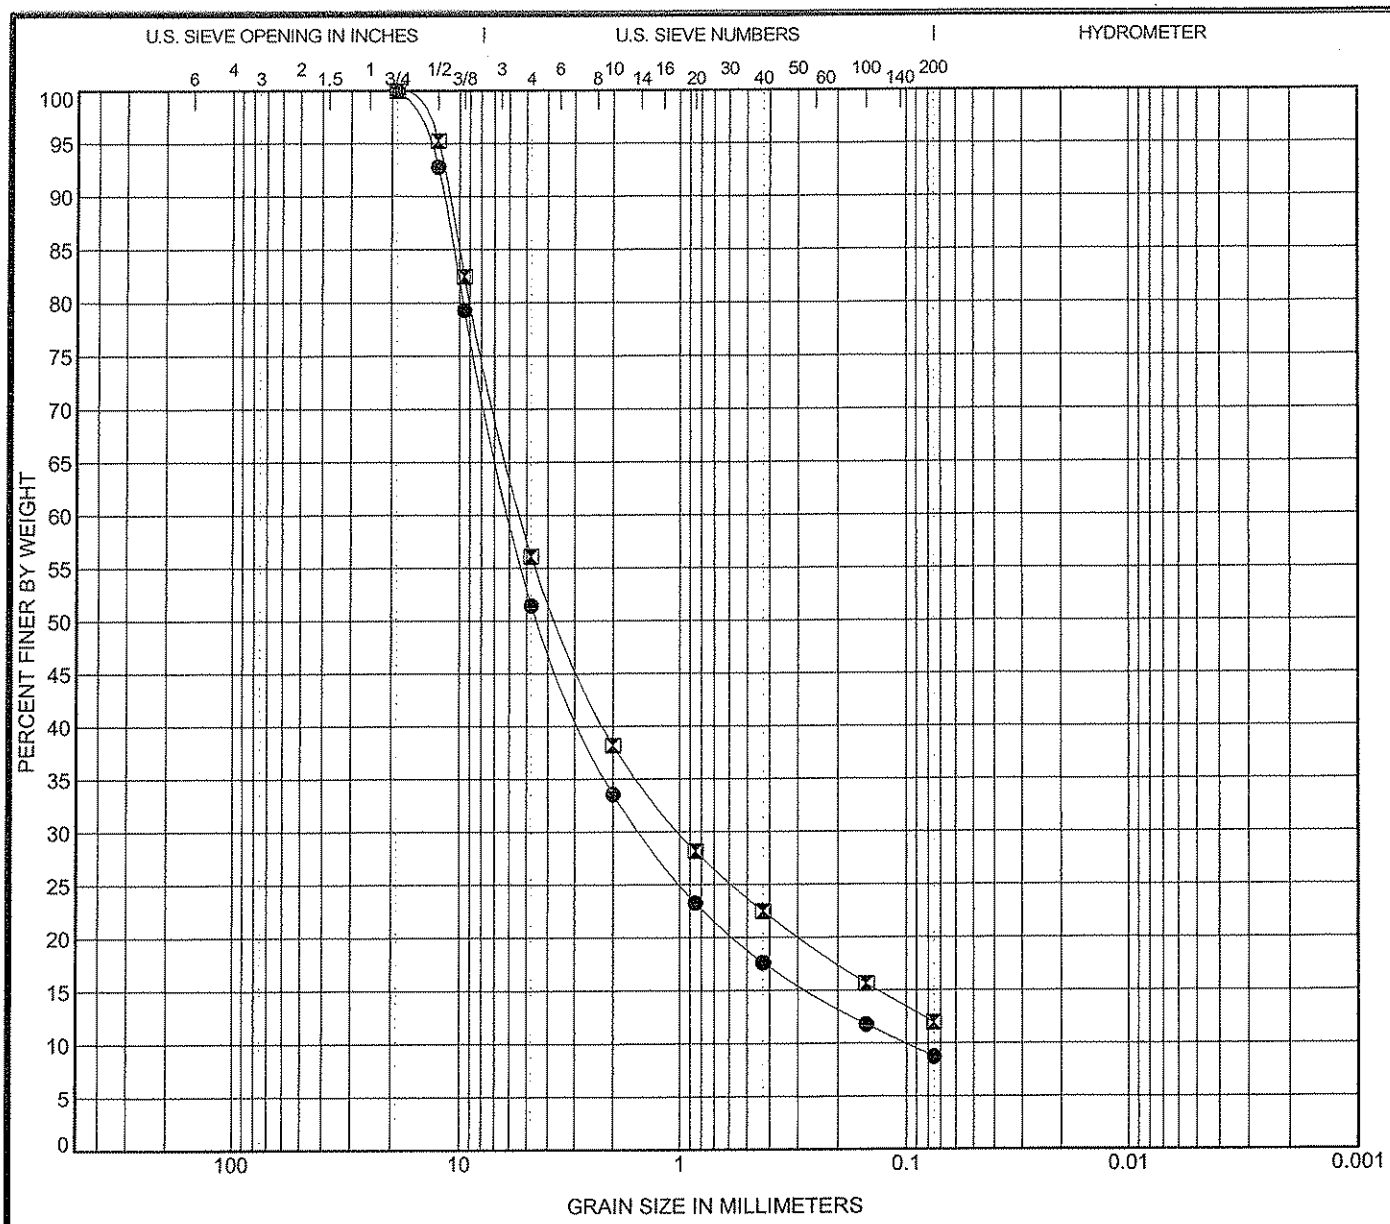

COBBLES	GRAVEL		SAND			SILT OR CLAY
	coarse	fine	coarse	medium	fine	

Specimen Identification		USCS Classification	LL	PL	PI	Cc	Cu
● TP-04 OX	15.0'	POORLY GRADED GRAVEL with CLAY and SAND (GP-GC)	28	20	8	3.77	58.75
⊠ TP-05 OX	0.0'	POORLY GRADED SAND with SILTY CLAY and GRAVEL (SP-SC)	27	20	7	3.64	101.88

Specimen Identification		D100	D60	D30	D10	MC %	%Gravel	%Sand	%Silt	%Clay
● TP-04 OX	15.0'	19	5.877	1.489	0.1	7.1	48.6	42.7	8.7	
⊠ TP-05 OX	0.0'	19	5.263	0.995		6.4	43.9	44.1	12.0	

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

GRAIN SIZE DISTRIBUTION

Project: **Yerington Mine**

Location: **Yerington, NV**

Project Number: **0155-21-1** Plate: 4e

US GRAIN SIZE2 0155221.GPJ US LAB.GDT 6/29/2009

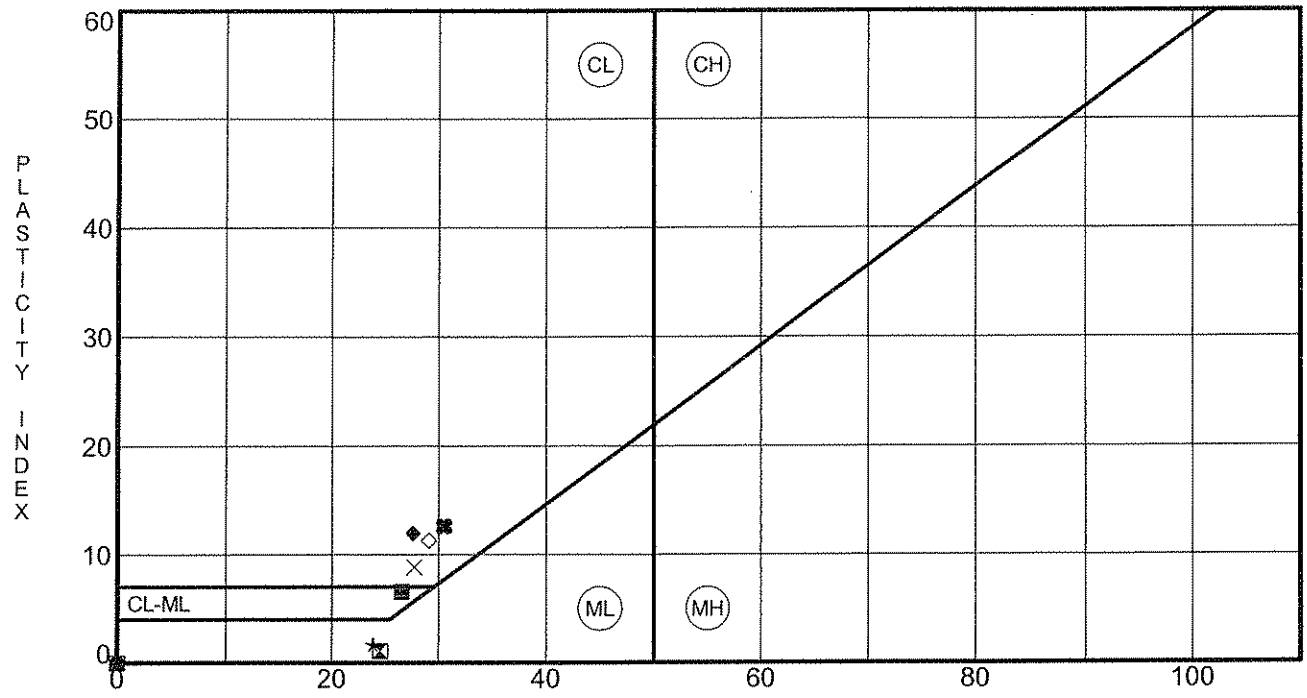

Specimen Depth in Feet.

	Specimen Identification		LL	PL	PI	Fines	USCS Classification
●	Clay Tails TP-09	2.0'	NP	NP	NP	33	SILTY SAND (SM)
⊠	Clay Tails TP-10	2.0'	25	23	2	97	SILT (ML)
▲	Clay Tails TP-11	0.0'	NP	NP	NP	92	SILT (ML)
★	Clay Tails TP-11	2.0'	24	22	2	90	SILT (ML)
⊙	Clay Tails TP-12	0.0'	NP	NP	NP	94	SILT (ML)
✿	NST TP-04	1.5'	NP	NP	NP	12	SILTY SAND (SM)
○	NST TP-05	0.0'	NP	NP	NP	64	SANDY SILT (ML)
△	NST TP-06	0.0'	NP	NP	NP	67	SANDY SILT (ML)
⊗	NST TP-07	1.5'	NP	NP	NP	61	SANDY SILT (ML)
⊕	NST TP-08	15.0'	NP	NP	NP	92	SILT (ML)
□	SST TP-01	0.0'	NP	NP	NP	18	SILTY SAND (SM)
⊖	SST TP-01	1.5'	NP	NP	NP	13	SILTY SAND (SM)
◕	SST TP-02	0.0'	NP	NP	NP	61	SANDY SILT (ML)
☆	SST TP-02	1.5'	NP	NP	NP	31	SILTY SAND (SM)
⊠	SST TP-03	1.5'	NP	NP	NP	67	SANDY SILT (ML)
■	TP-01 OX	0.0'	27	20	7	9	POORLY GRADED SAND with SILTY CLAY and GRAVEL (SP-SC
◆	TP-01 OX	5.0'	28	16	12	8	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)
◇	TP-02 OX	20.0'	29	18	11	9	POORLY GRADED GRAVEL with CLAY and SAND (GP-GC)
×	TP-03 OX	0.0'	28	19	9	11	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)
✖	TP-03 OX	10.0'	31	18	13	10	POORLY GRADED SAND with CLAY and GRAVEL (SP-SC)

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

ATTERBERG LIMITS RESULTS

Project: **Yerington Mine**
Location: **Yerington, NV**
Project Number: **0155-21-1** Plate: 4f

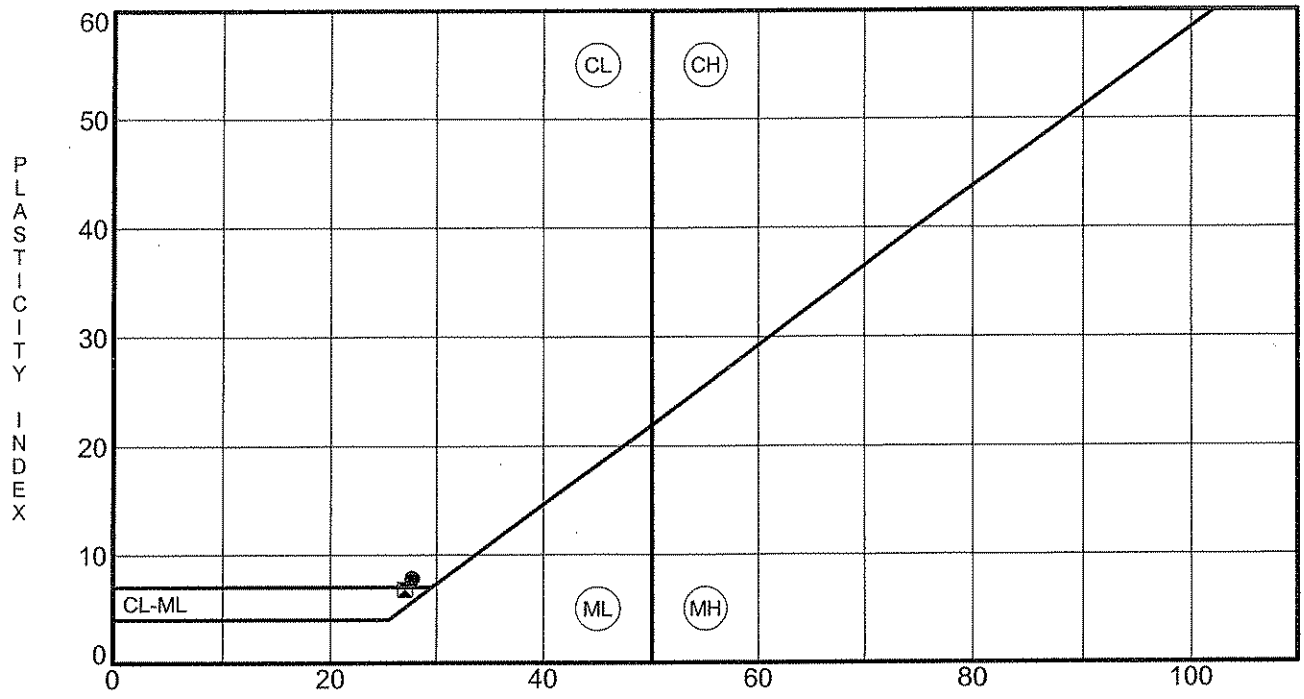

Specimen Depth in Feet.

	Specimen Identification		LL	PL	PI	Fines	USCS Classification
●	TP-04 OX	15.0'	28	20	8	9	POORLY GRADED GRAVEL with CLAY and SAND (GP-GC)
☒	TP-05 OX	0.0'	27	20	7	12	POORLY GRADED SAND with SILTY CLAY and GRAVEL (SP-SC

Black Eagle Consulting, Inc.
1345 Capital Blvd., Suite A
Reno, Nevada 89502-7140
Telephone: (775) 359-6600
Fax: (775) 359-7766

ATTERBERG LIMITS RESULTS

Project: **Yerington Mine**
Location: **Yerington, NV**
Project Number: **0155-21-1** Plate: 4g

COMPACTION TEST REPORT

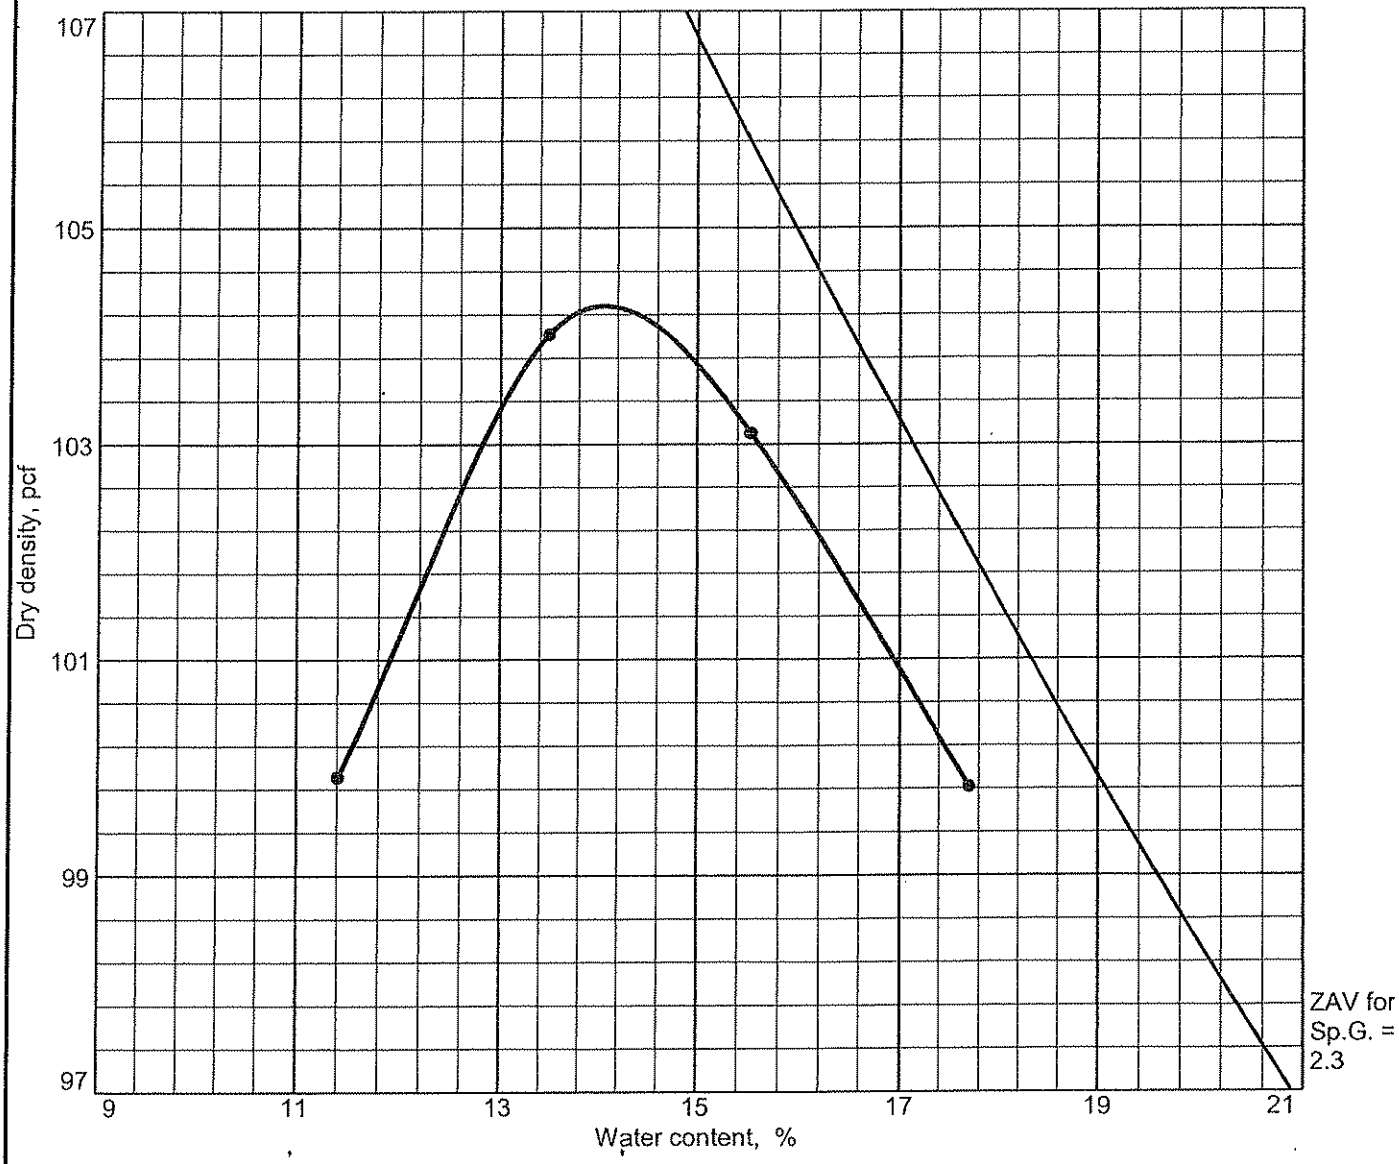

Test specification: ASTM D 1557-00 Method A Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > No.4	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	SM				No Value	Non Plastic	0.0	17.6

TEST RESULTS

Maximum dry density = 104.3 pcf

Optimum moisture = 14.1 %

MATERIAL DESCRIPTION

Silty Sand

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** SST TP-01 **Sample No.:** Bulk **Elev./Depth:** 0.0' - 20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5a

COMPACTION TEST REPORT

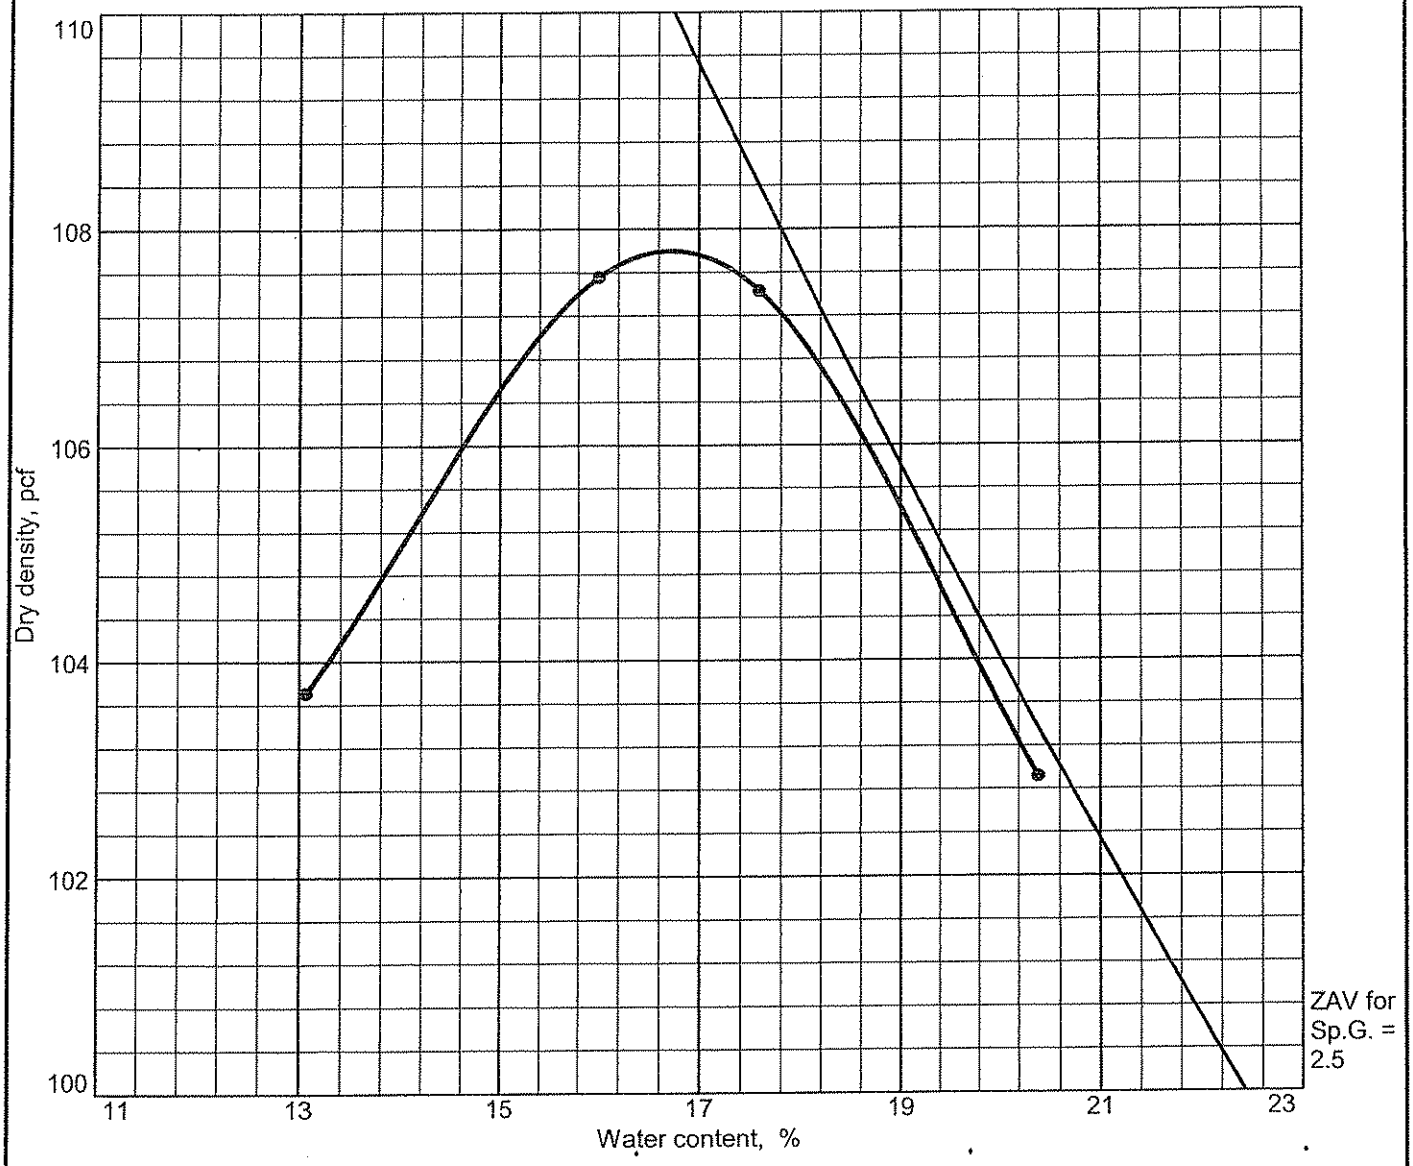

Test specification: ASTM D 1557-00 Method A Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > No.4	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	ML				No Value	Non Plastic		

TEST RESULTS

Maximum dry density = 107.8 pcf

Optimum moisture = 16.7 %

MATERIAL DESCRIPTION

Sandy Silt

Project No. 0155-21-1 **Client:** Brown & Caldwell

Project: Yerington Mine

● **Source:** SST TP-02 **Sample No.:** Bulk **Elev./Depth:** 0.0' - 20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5b

COMPACTION TEST REPORT

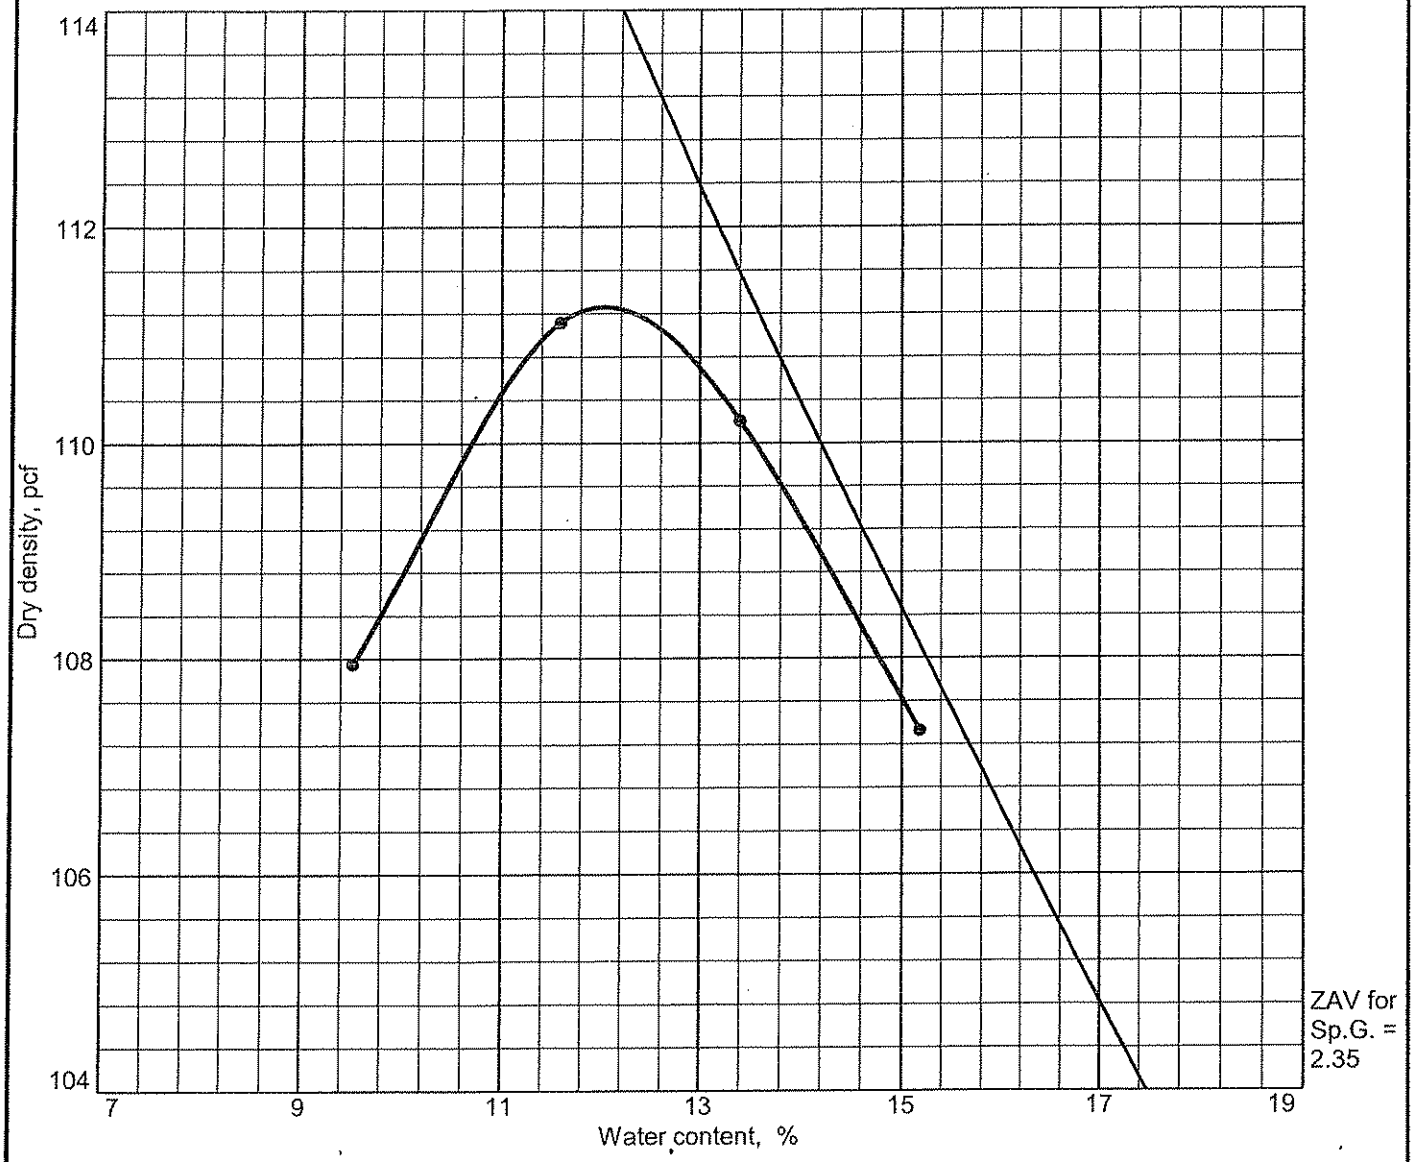

Test specification: ASTM D 1557-00 Method B Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/8 in.	% < No.200
	USCS	AASHTO						
0.0' -20.0'	ML				No Value	Non Plastic	4.0	63.6

TEST RESULTS

Maximum dry density = 111.3 pcf

Optimum moisture = 12.0 %

MATERIAL DESCRIPTION

Sandy Silt

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** NST TP-05 **Sample No.:** Bulk **Elev./Depth:** 0.0' -20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5c

COMPACTION TEST REPORT

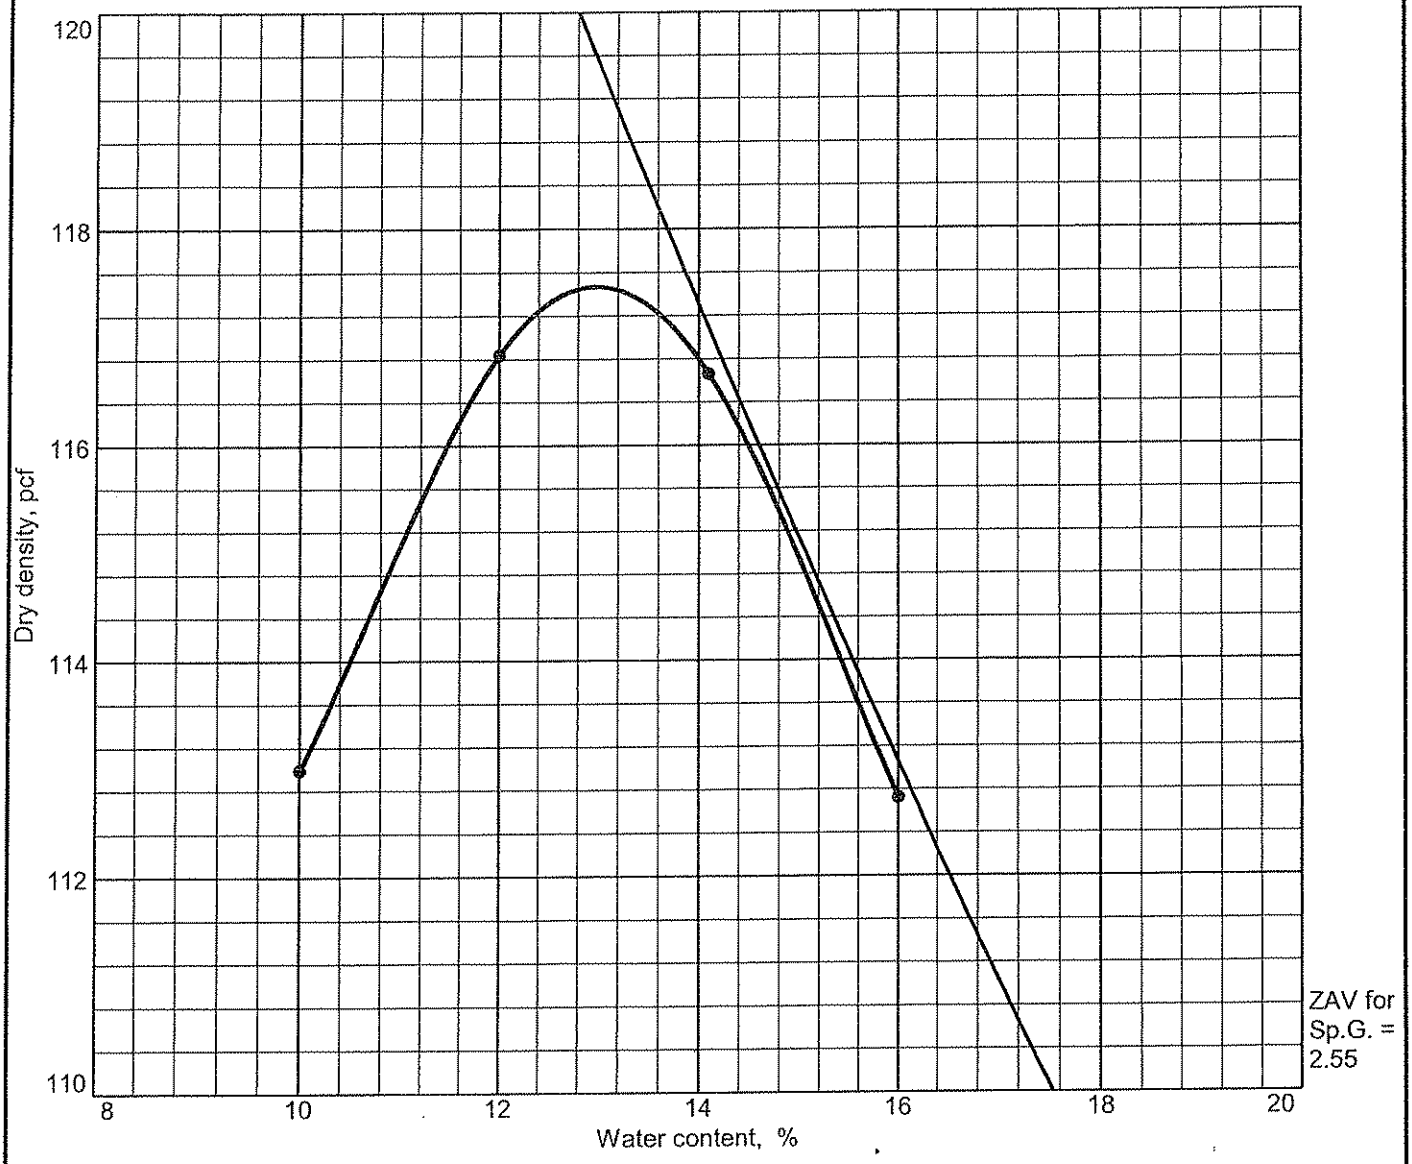

Test specification: ASTM D 1557-00 Method A Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > No.4	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	ML				No Value	Non Plastic		

TEST RESULTS	MATERIAL DESCRIPTION
Maximum dry density = 117.5 pcf Optimum moisture = 13.0 %	Sandy Silt

Project No. 0155-21-1 **Client:** Brown & Caldwell
Project: Yerington Mine

● **Source:** NST TP-06 **Sample No.:** Composite **Elev./Depth:** 0.0' - 20.0'

Remarks:
Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.
Reno, Nevada

Plate 5d

COMPACTION TEST REPORT

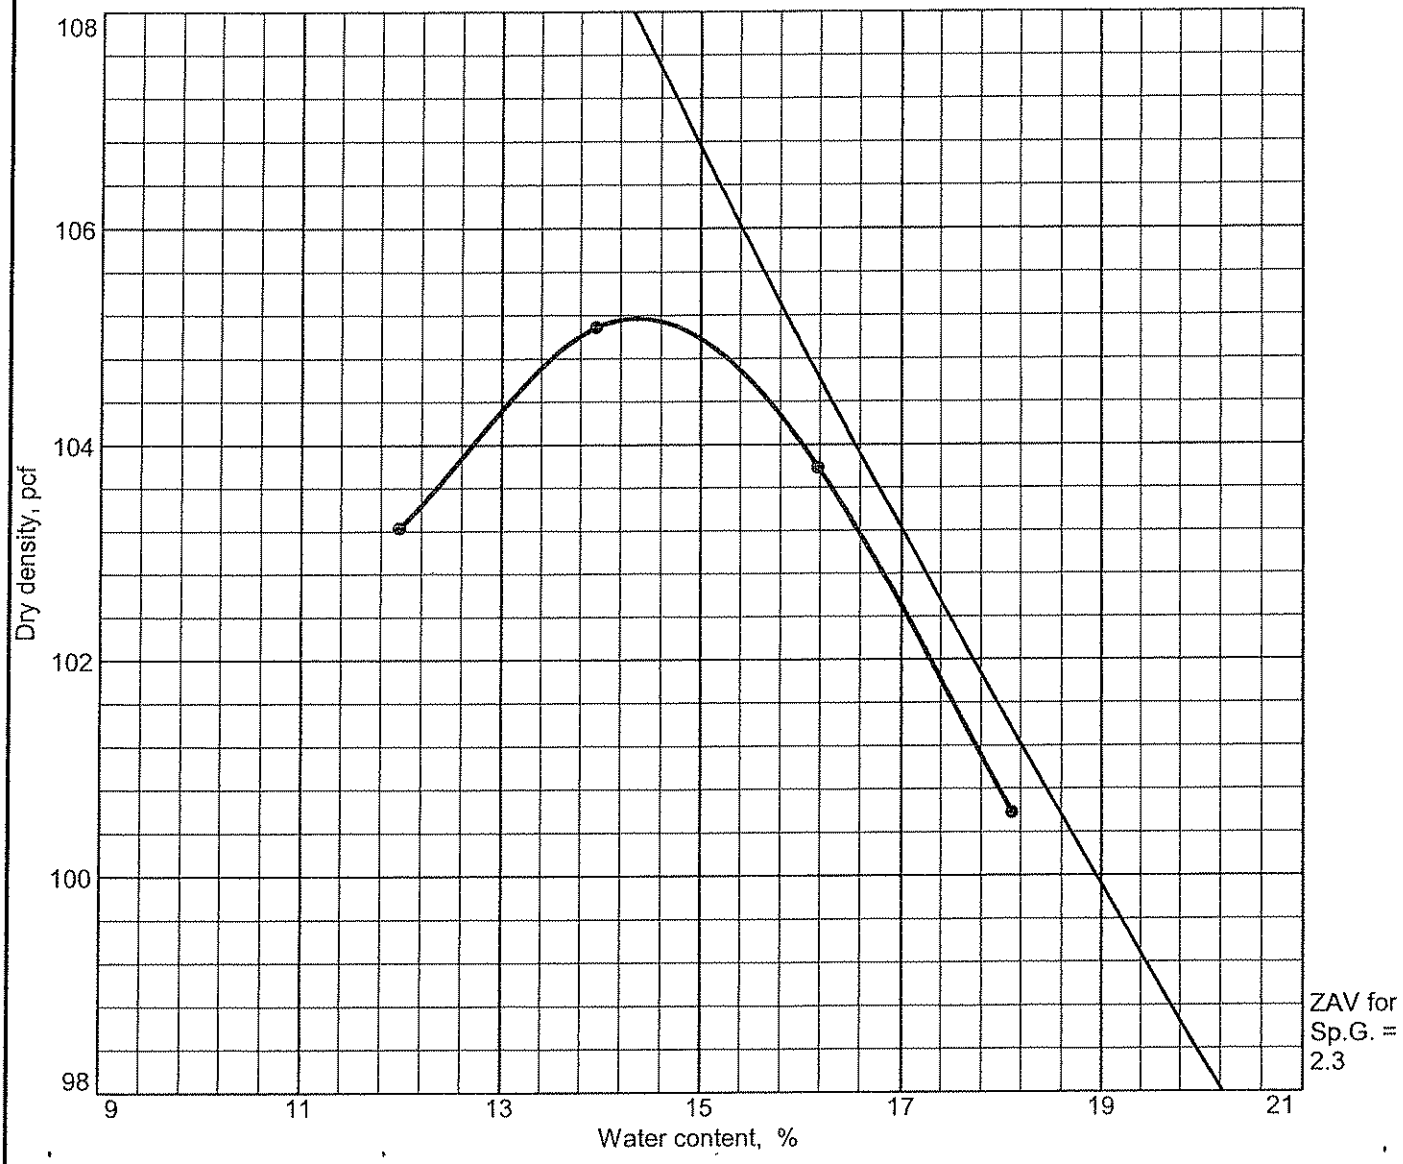

Test specification: ASTM D 1557-00 Method B Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/8 in.	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	ML				No Value	Non Plastic	0.0	92.3

TEST RESULTS	MATERIAL DESCRIPTION
Maximum dry density = 105.2 pcf Optimum moisture = 14.4 %	Silt

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** TP-11 Clay Tails **Sample No.:** Bulk **Elev./Depth:** 0.0' - 20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5e

COMPACTION TEST REPORT

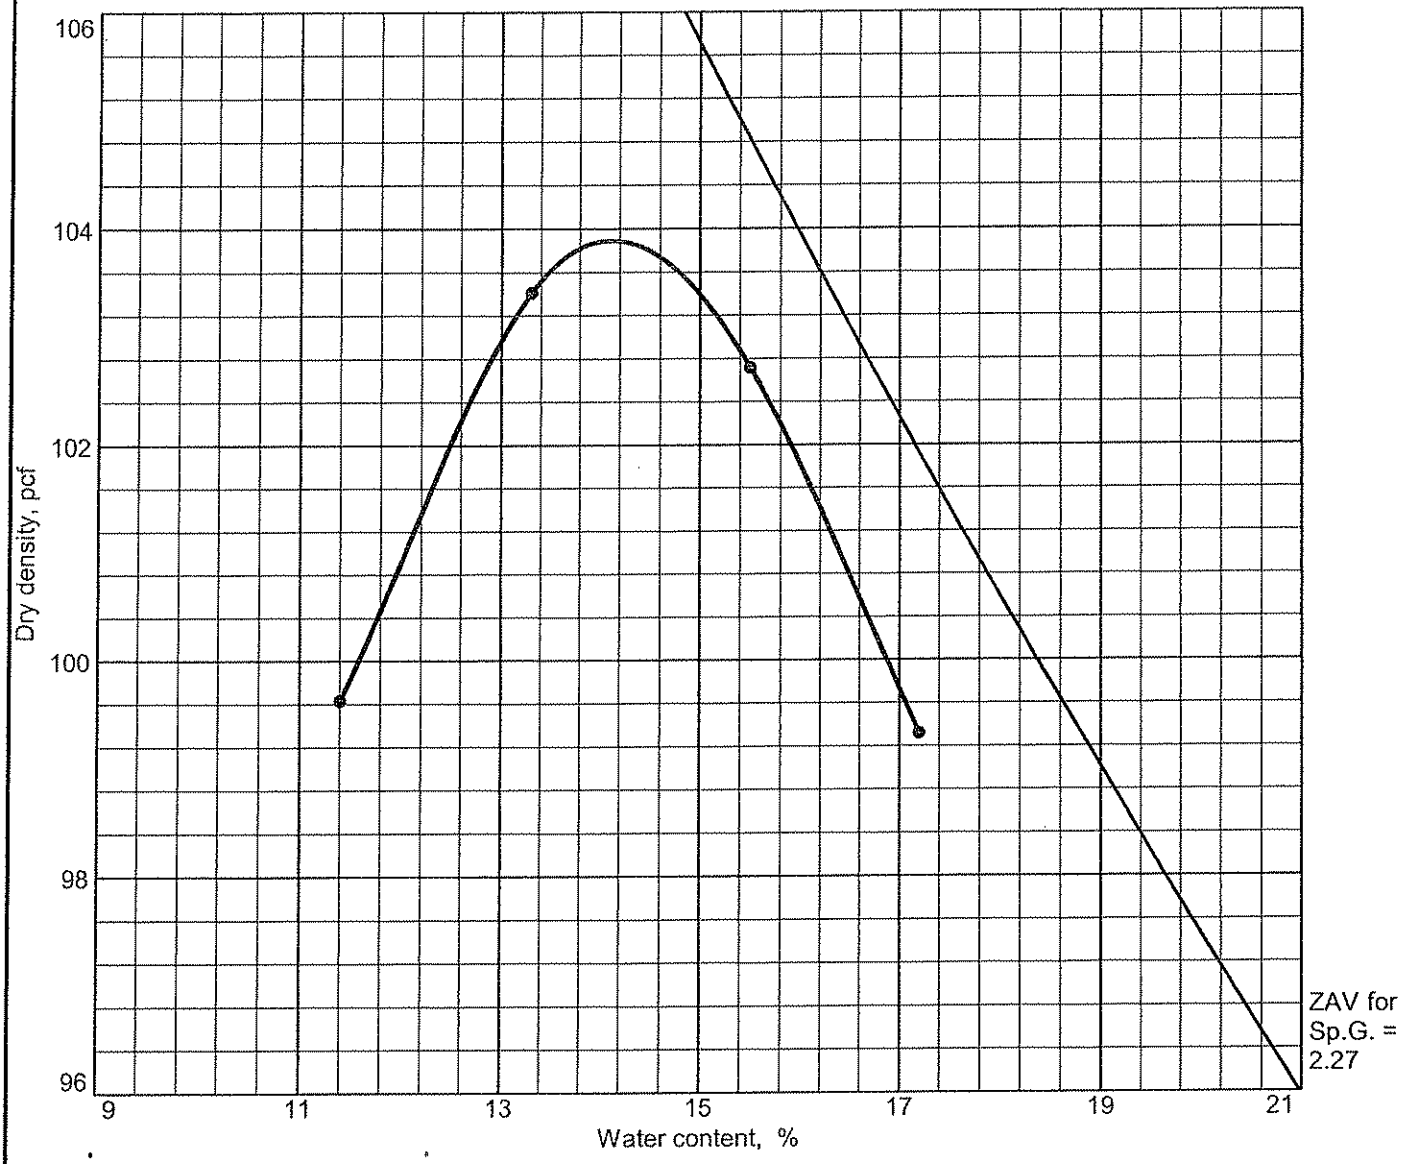

Test specification: ASTM D 1557-00 Method B Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/8 in.	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	ML				No Value	Non Plastic	0.0	93.9

TEST RESULTS

Maximum dry density = 103.9 pcf

Optimum moisture = 14.1 %

MATERIAL DESCRIPTION

Silt

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** TP-12 Clay Tails **Sample No.:** Bulk **Elev./Depth:** 0.0' - 20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5f

COMPACTION TEST REPORT

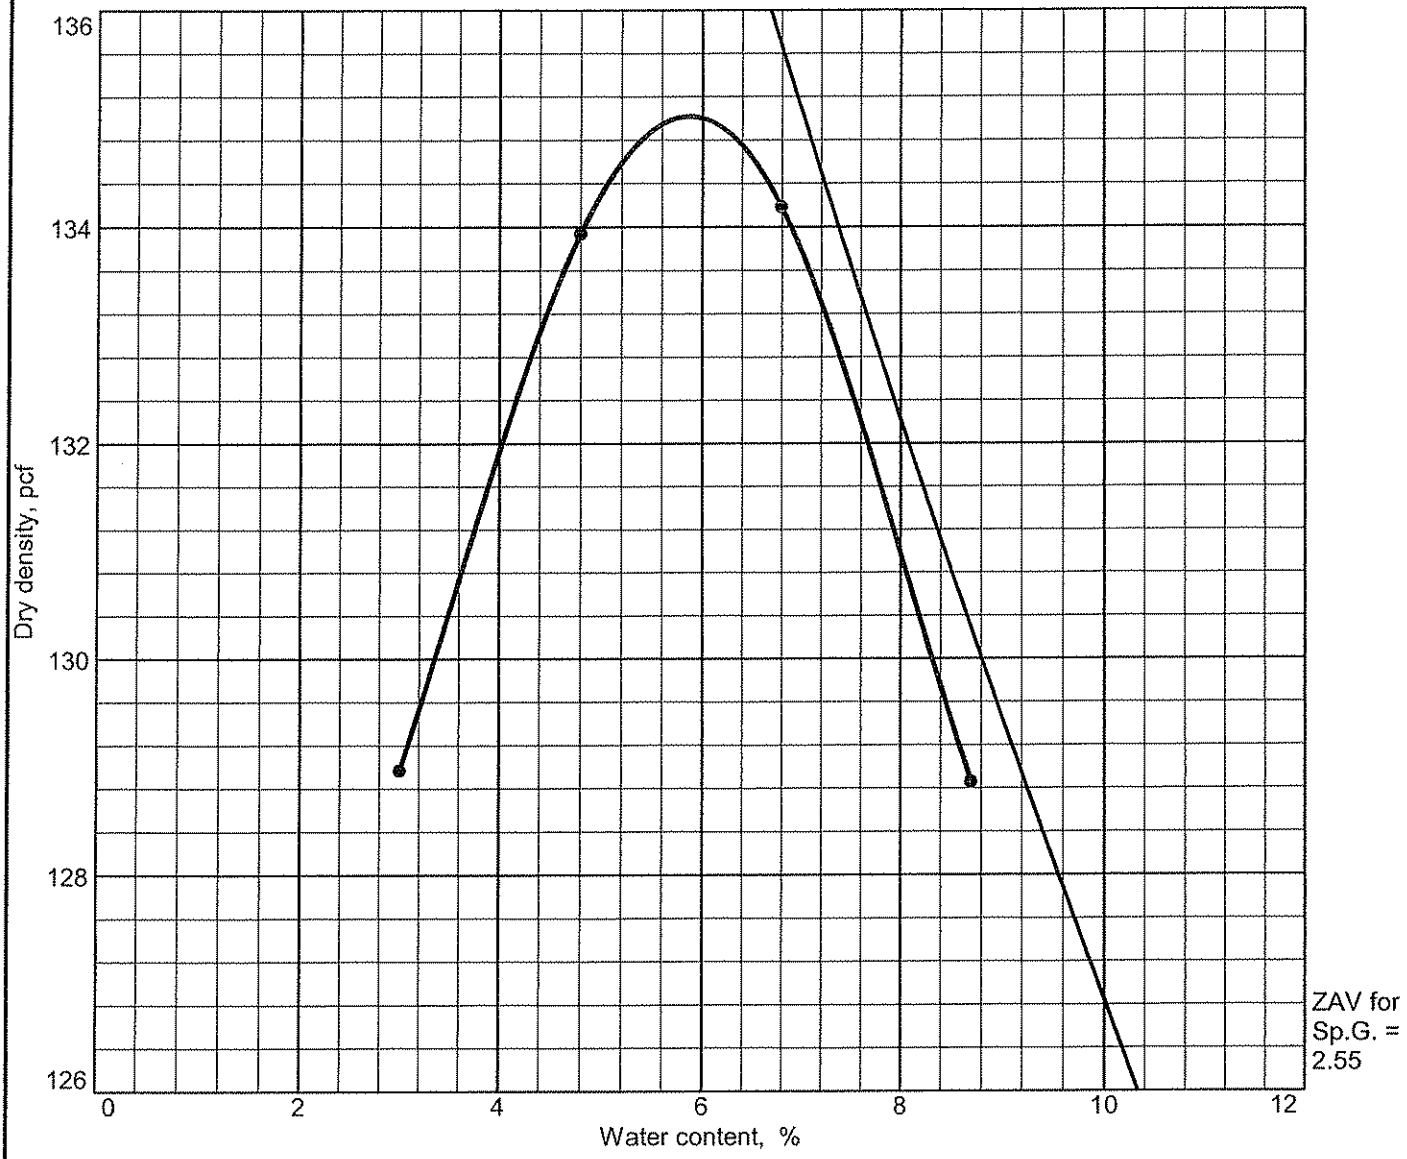

Test specification: ASTM D 1557-00 Method C Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/4 in.	% < No.200
	USCS	AASHTO						
0.0' - 20.0'	GP - GC		4.8		28	10	0.0	8.4

TEST RESULTS

Maximum dry density = 135.0 pcf

Optimum moisture = 5.9 %

MATERIAL DESCRIPTION

Poorly Graded Gravel with Clay and Sand

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** TP-01 OX **Sample No.:** Bulk **Elev./Depth:** 0.0' - 20.0'

Remarks:

Laboratory Number 1258

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5g

COMPACTION TEST REPORT

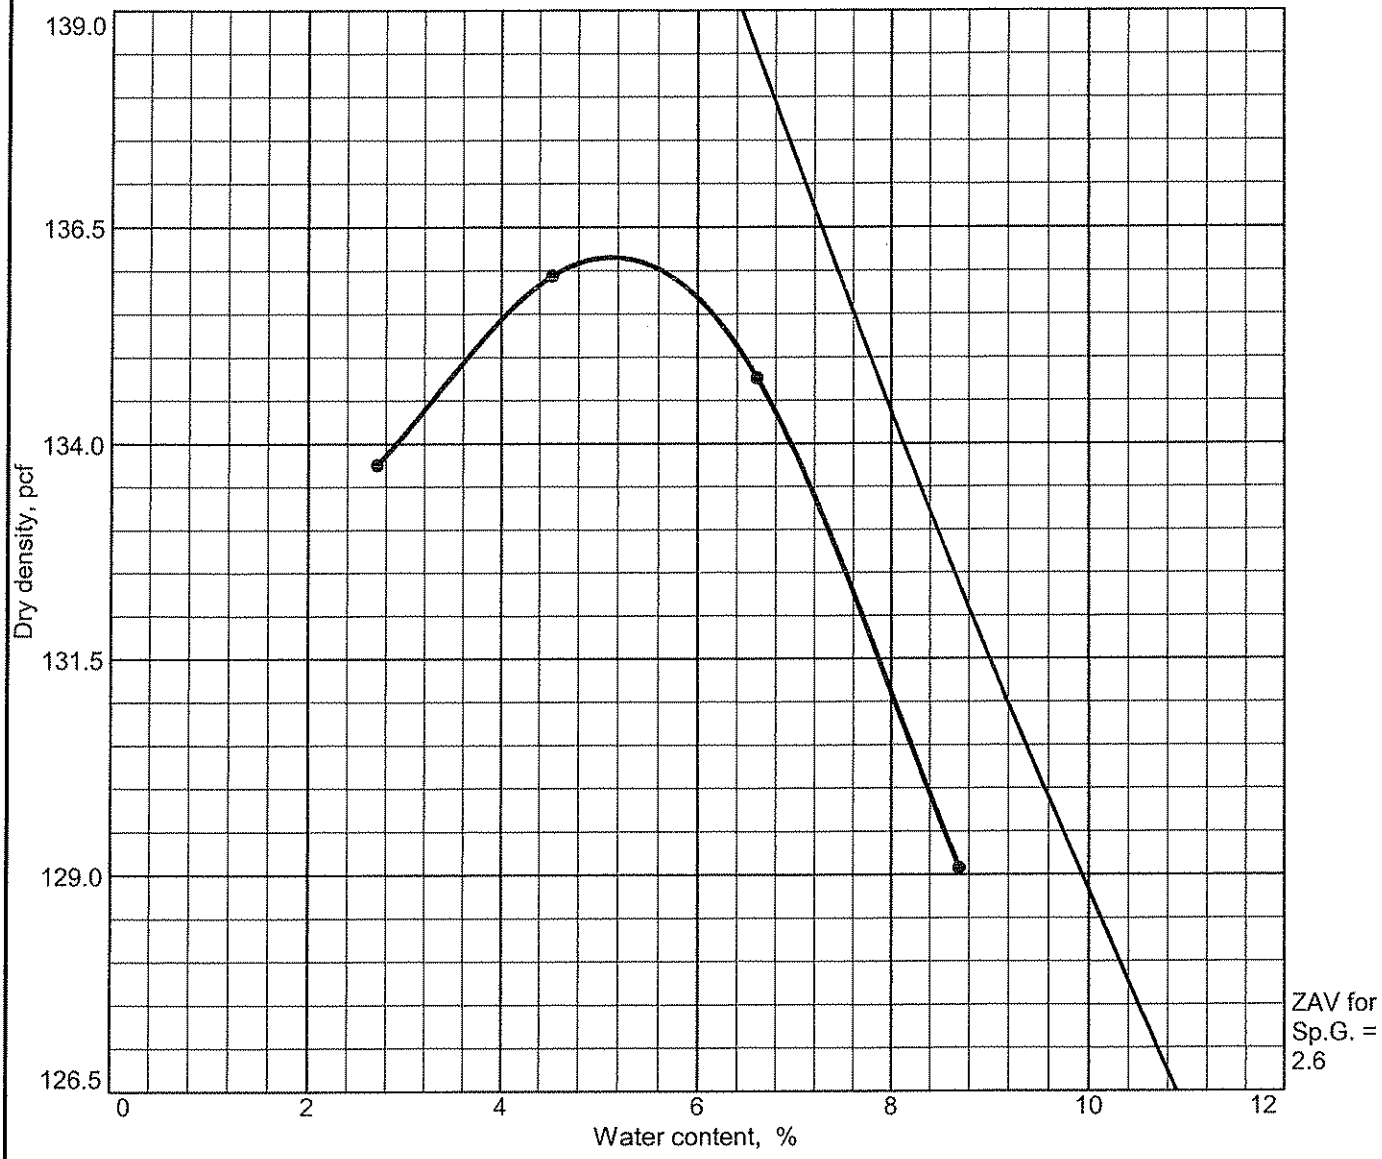

Test specification: ASTM D 1557-00 Method C Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/4 in.	% < No.200
	USCS	AASHTO						
0.0' -20.0'	SP - SC				28	9	0.0	10.9

TEST RESULTS	MATERIAL DESCRIPTION
Maximum dry density = 136.2 pcf Optimum moisture = 5.1 %	Poorly Graded Sand with Clay and Gravel

Project No. 0155-21-1 **Client:**

Project: Yerington Mine

● **Source:** TP-03 OX **Sample No.:** Bulk **Elev./Depth:** 0.0' -20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5h

COMPACTION TEST REPORT

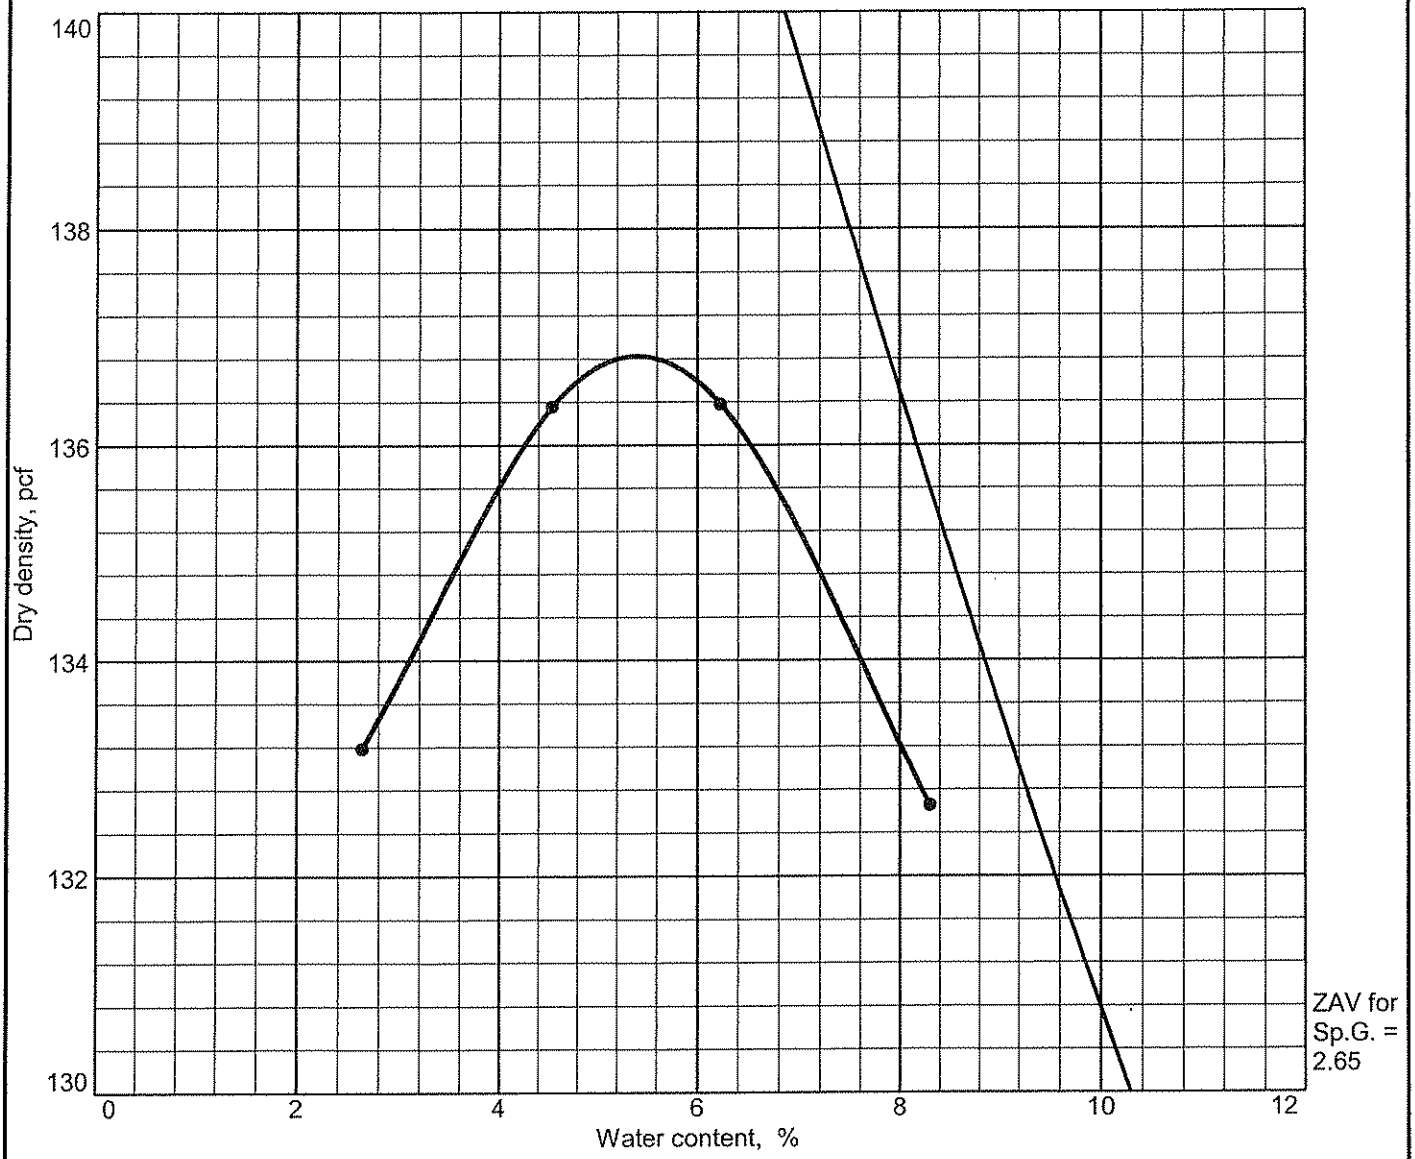

Test specification: ASTM D 1557-00 Method C Modified

Elev/ Depth	Classification		Nat. Moist.	Sp.G.	LL	PI	% > 3/4 in.	% < No.200
	USCS	AASHTO						
0.0 ' - 20.0'	SP - SC				27	7	0.0	12

TEST RESULTS

Maximum dry density = 136.8 pcf

Optimum moisture = 5.4 %

MATERIAL DESCRIPTION

Poorly Graded Sand with Silty Clay and Gravel

Project No. 0155-21-1 **Client:** Brown and Caldwell

Project: Yerington Mine

● **Source:** TP-05 OX **Sample No.:** Bulk **Elev./Depth:** 0.0 ' - 20.0'

Remarks:

Laboratory Number 1273

BLACK EAGLE CONSULTING, INC.

Reno, Nevada

Plate 5i

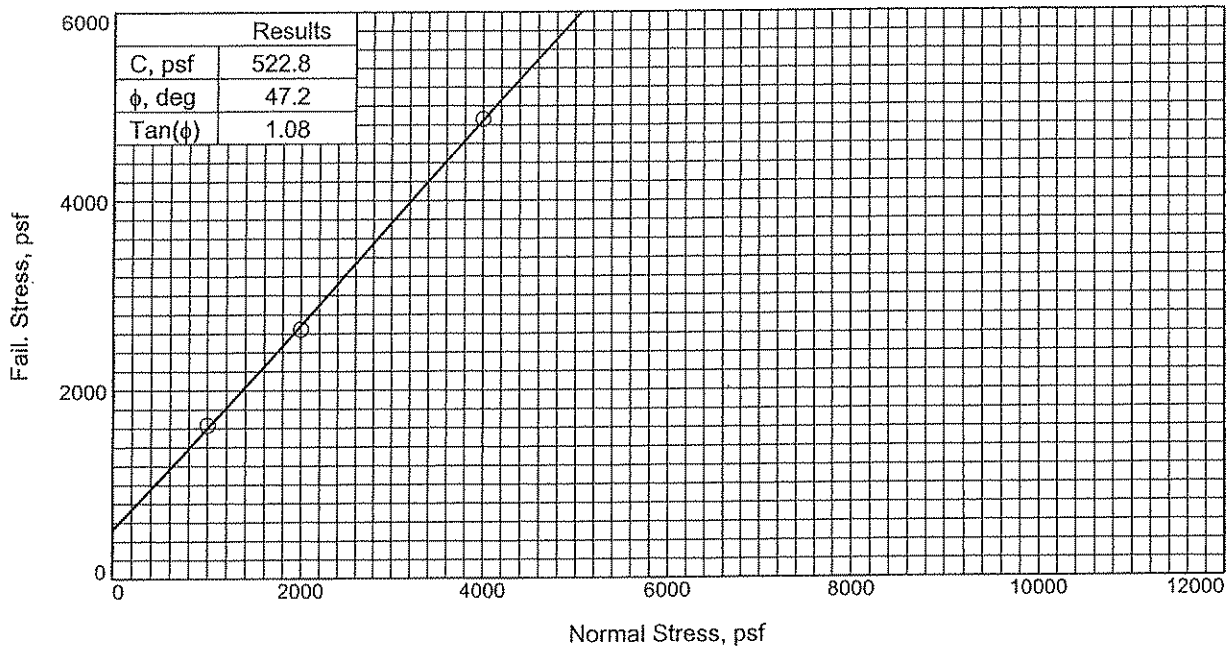

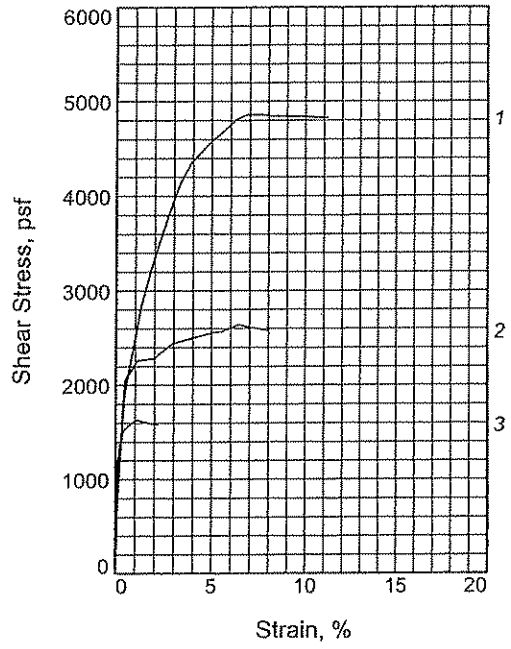

Sample No.		1	2	3
Initial	Water Content, %	11.3	11.3	11.3
	Dry Density, pcf	88.7	88.1	89.3
	Saturation, %	35.7	35.3	36.3
	Void Ratio	0.8215	0.8322	0.8078
	Diameter, in.	2.420	2.420	2.420
	Height, in.	1.000	1.000	1.000
At Test	Water Content, %	26.5	28.0	26.8
	Dry Density, pcf	95.7	91.5	92.1
	Saturation, %	99.7	94.7	92.1
	Void Ratio	0.6869	0.7655	0.7529
	Diameter, in.	2.420	2.420	2.420
	Height, in.	0.926	0.964	0.970
Normal Stress, psf		4000.0	2000.0	1000.0
Fail. Stress, psf		4858.9	2642.3	1631.1
Strain, %		7.2	6.4	1.1
Ult. Stress, psf				
Strain, %				
Strain rate, in./min.		0.002	0.002	0.002

Sample Type: Remolded
Description: Silty Sand

LL= No Value **PI=** Non Plastic
Specific Gravity= 2.587
Remarks: Laboratory Number 1273

Client: Brown & Caldwell

Project: Yerington Mine

Source of Sample: SST TP-01 **Depth:** 0.0' - 20.0'
Sample Number: Bulk
Proj. No.: 0155-21-1 **Date Sampled:**

DIRECT SHEAR TEST REPORT

BLACK EAGLE CONSULTING, INC.

Plate 6a

Tested By: G. Bomberger

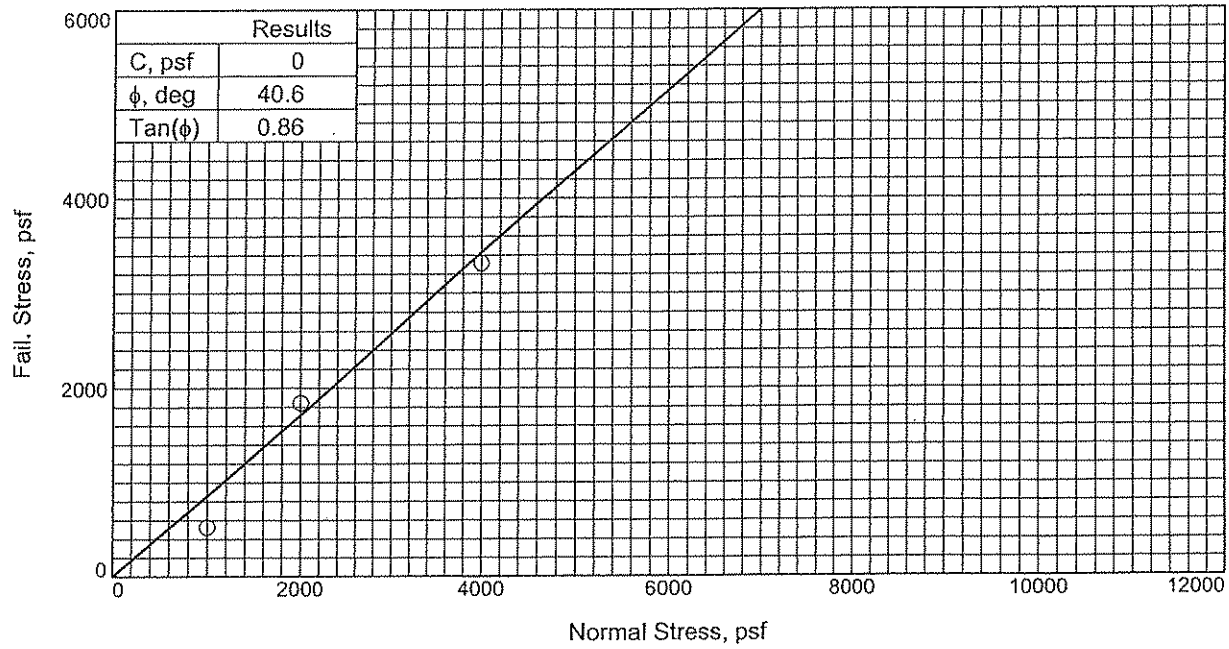

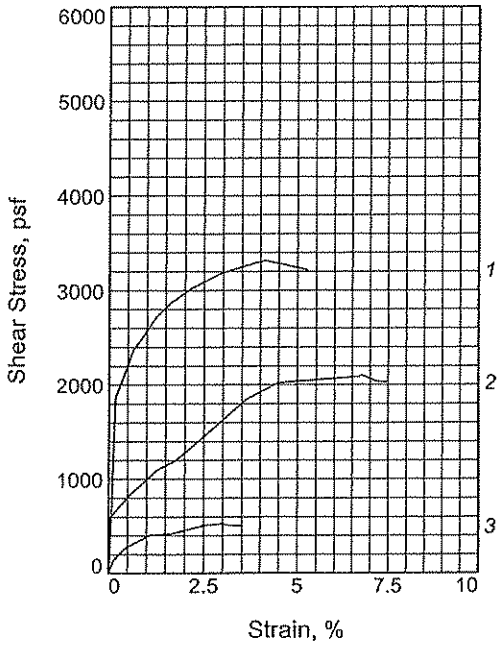

Sample No.		1	2	3
Initial	Water Content, %	11.3	11.3	11.3
	Dry Density, pcf	101.2	102.3	102.1
	Saturation, %	47.9	49.2	49.0
	Void Ratio	0.6222	0.6057	0.6081
	Diameter, in.	2.420	2.420	2.420
	Height, in.	1.000	1.000	1.000
At Test	Water Content, %	18.4	18.8	21.8
	Dry Density, pcf	109.3	108.3	103.6
	Saturation, %	96.2	95.9	97.8
	Void Ratio	0.5020	0.5166	0.5857
	Diameter, in.	2.420	2.420	2.420
	Height, in.	0.926	0.945	0.986
Normal Stress, psf		4000.0	2000.0	1000.0
Fail. Stress, psf		3315.4	1844.0	526.0
Strain, %		4.1	3.6	3.0
Ult. Stress, psf				
Strain, %				
Strain rate, in./min.		0.002	0.002	0.002

Sample Type: Remolded
Description: Sandy Silt

LL= No Value **PI=** Non Plastic
Specific Gravity= 2.631
Remarks: Laboratory Number 1273

Client: Brown & Caldwell

Project: Yerington Mine

Source of Sample: SST TP-02 **Depth:** 0.0' - 20.0'
Sample Number: Bulk
Proj. No.: 0155-21-1 **Date Sampled:**

DIRECT SHEAR TEST REPORT

BLACK EAGLE CONSULTING, INC.

Plate 6b

Tested By: G. Bomberger

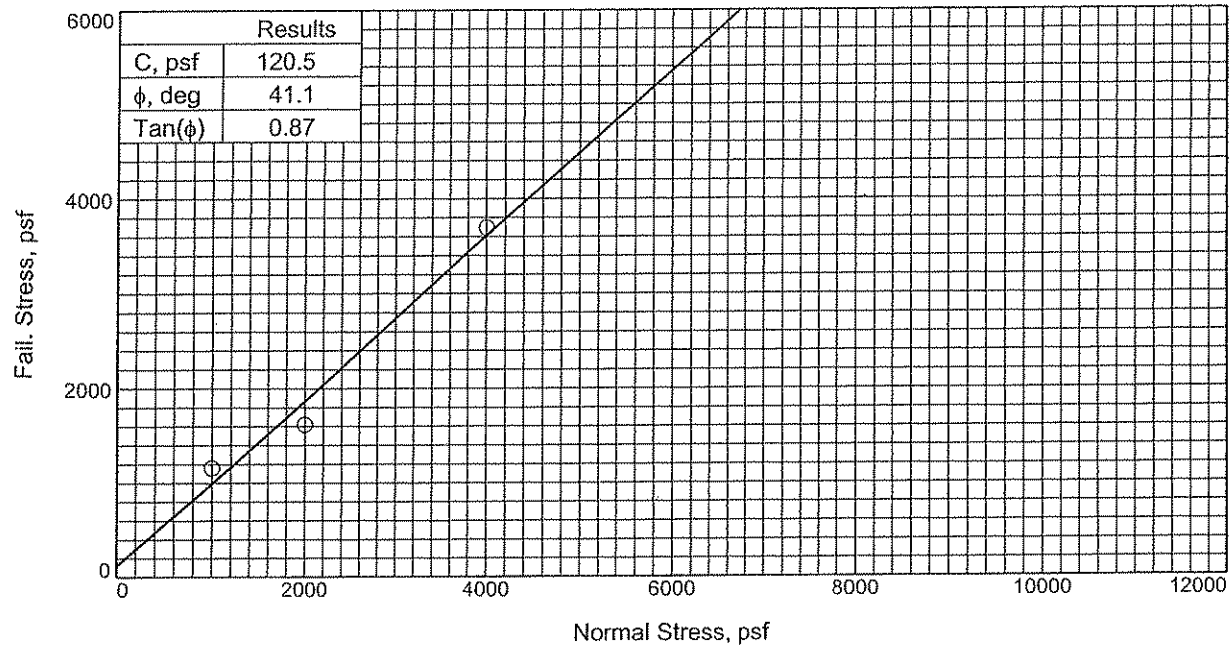

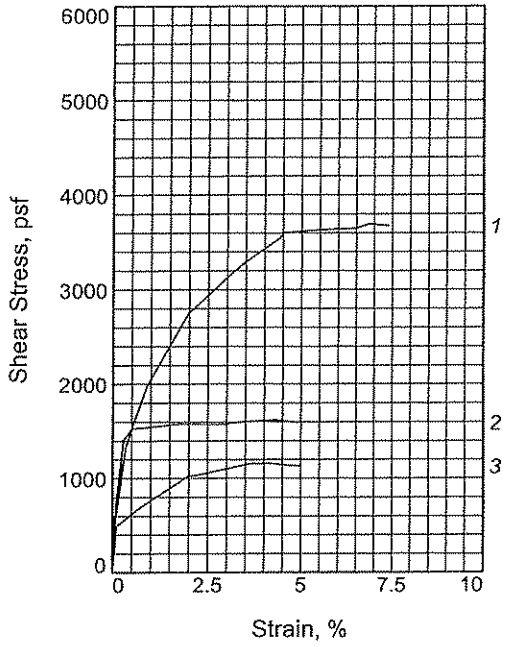

Sample No.		1	2	3
Initial	Water Content, %	7.1	7.1	7.1
	Dry Density, pcf	100.0	99.0	98.8
	Saturation, %	29.5	28.7	28.5
	Void Ratio	0.6233	0.6398	0.6436
	Diameter, in.	2.420	2.420	2.420
	Height, in.	1.000	1.000	1.000
At Test	Water Content, %	16.4	18.1	18.8
	Dry Density, pcf	112.3	109.4	108.1
	Saturation, %	95.8	97.4	97.0
	Void Ratio	0.4454	0.4837	0.5028
	Diameter, in.	2.420	2.420	2.420
	Height, in.	0.890	0.905	0.914
Normal Stress, psf		4000.0	2000.0	1000.0
Fail. Stress, psf		3694.2	1618.6	1158.4
Strain, %		6.9	4.3	3.7
Ult. Stress, psf				
Strain, %				
Strain rate, in./min.		0.002	0.002	0.002

Sample Type: Remolded
Description: Sandy Silt

LL= No Value **PI=** Non Plastic
Specific Gravity= 2.601
Remarks: Laboratory Number 1273

Client: Brown & Caldwell

Project: Yerington Mine

Source of Sample: NST TP-05 **Depth:** 0.0' - 20.0'
Sample Number: Bulk
Proj. No.: 0155-21-1 **Date Sampled:**

DIRECT SHEAR TEST REPORT

BLACK EAGLE CONSULTING, INC.

Plate 6c

Tested By: G. Bomberger

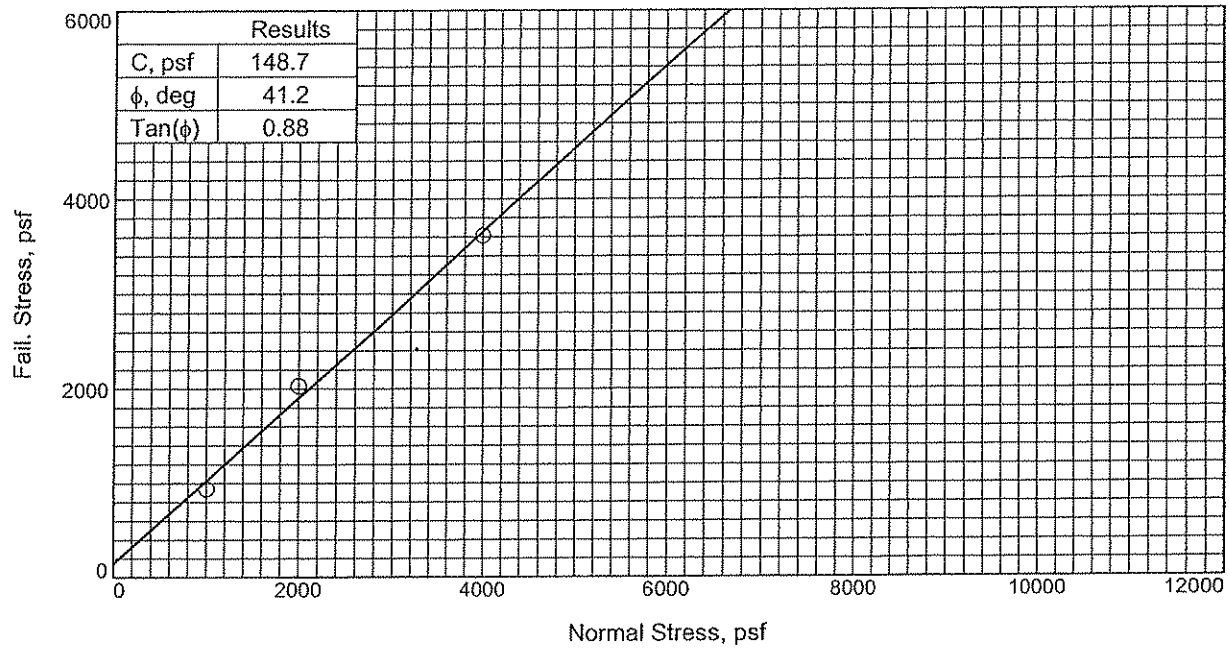

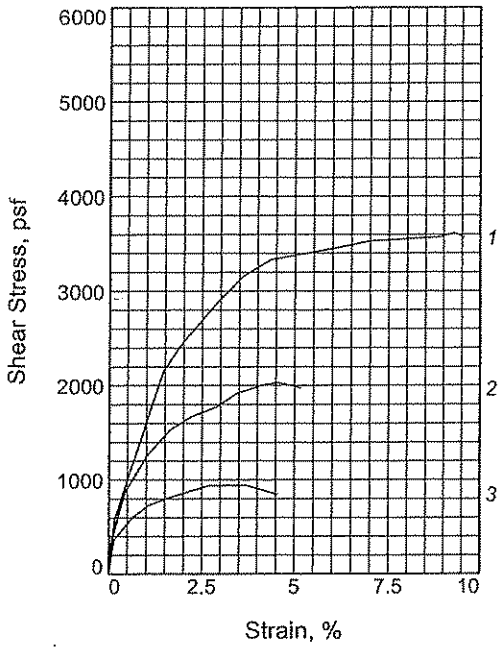

Sample No.		1	2	3
Initial	Water Content, %	16.4	16.4	16.4
	Dry Density, pcf	95.4	94.0	95.0
	Saturation, %	60.6	58.5	60.0
	Void Ratio	0.7083	0.7341	0.7160
	Diameter, in.	2.420	2.420	2.420
	Height, in.	1.000	1.000	1.000
At Test	Water Content, %	20.3	24.5	24.9
	Dry Density, pcf	105.2	99.1	98.4
	Saturation, %	96.4	99.2	99.1
	Void Ratio	0.5492	0.6441	0.6559
	Diameter, in.	2.420	2.420	2.420
	Height, in.	0.907	0.948	0.965
Normal Stress, psf		4000.0	2000.0	1000.0
Fail. Stress, psf		3612.8	2031.8	939.2
Strain, %		9.3	4.6	2.7
Ult. Stress, psf				
Strain, %				
Strain rate, in./min.		0.002	0.002	0.002

Sample Type: Remolded
Description: Sandy Silt

LL= No Value **PI=** Non Plastic
Specific Gravity= 2.610
Remarks: Laboratory Number 1273

Plate 6d

Client: Brown & Caldwell

Project: Yerington Mine

Source of Sample: NST TP-06 **Depth:** 0.0' - 20.0'
Sample Number: Composite
Proj. No.: 0155-21-1 **Date Sampled:**

DIRECT SHEAR TEST REPORT

BLACK EAGLE CONSULTING, INC.

Tested By: G. Bomberger

Hydraulic Conductivity
ASTM D 5084
Method C: Falling Head Rising Tailwater

Job No:	698-001	**Boring:**	NST-TP-06	**Date:**	06/11/09
Client:	Black Eagle Consulting	**Sample:**	Composite	**By:**	MD/PJ
Project:	0155-21-1	**Depth, ft.:**		**Remolded:**	Target= 90% of 117.5 pcf @ 13%(OPT).

Visual Classification: Sandy Silt

Max Sample Pressures, psi:

Cell:	Bottom	Top	Avg. Sigma3
84	79	79	5

Date	Minutes	Head, (in)	K,cm/sec
6/8/2009	0.00	15.00	Start of Test
6/8/2009	4.00	10.70	1.2E-04
6/8/2009	10.00	8.00	9.3E-05
6/8/2009	13.00	7.00	8.7E-05
6/8/2009	41.00	1.60	8.1E-05
6/8/2009	11.00	7.70	9.0E-05
6/8/2009	23.00	3.80	8.8E-05
6/8/2009	45.00	1.00	8.9E-05

B: = >0.95 ("B" is an indication of saturation)

Max Hydraulic Gradient: = 5

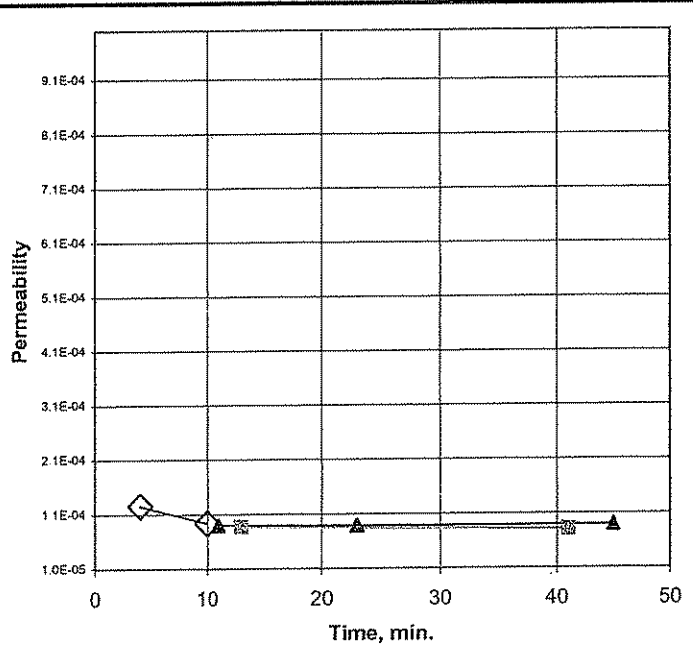

Average Permeability: 9.E-05 cm/sec

Sample Data:	Initial	Final
Height, in	3.00	3.00
Diameter, in	2.38	2.38
Area, in2	4.43	4.45
Volume in3	13.29	13.35
Total Volume, cc	217.8	218.7
Volume Solids, cc	140.3	140.3
Volume Voids, cc	77.4	78.4
Void Ratio	0.6	0.6
Total Porosity, %	35.6	35.8
Air-Filled Porosity, %	12.1	-1.0
Water-Filled Porosity,%	23.4	36.8
Saturation, %	65.9	102.7
Specific Gravity	2.610	2.610
Wet Weight, gm	417.3	446.8
Dry Weight, gm	366.3	366.3
Tare, gm	0.00	0.00
Moisture, %	13.9	22.0
Dry Density, pcf	104.9	104.5

Remarks: Due to slumping of the sample after the confining pressure was released, the final sample dimensions and associated values are approximate.

Hydraulic Conductivity
ASTM D 5084
Method C: Falling Head Rising Tailwater

Job No:	698-001	**Boring:**	SSTP-02	**Date:**	06/11/09
Client:	Black Eagle Consulting	**Sample:**	Bulk	**By:**	MD/PJ
Project:	0155-21-1	**Depth, ft.:**	0-20	**Remolded:**	Target= 90% of 107.8 pcf @ 16% (OPT).

Visual Classification: Silty Sand

Max Sample Pressures, psi:

Cell:	Bottom	Top	Avg. Sigma3
74	69	69	5

Date	Minutes	Head, (in)	K,cm/sec
6/8/2009	0.00	15.00	Start of Test
6/8/2009	1.00	12.00	3.2E-04
6/8/2009	4.00	6.40	3.1E-04
6/8/2009	7.00	3.50	3.0E-04
6/8/2009	1.00	12.30	2.9E-04
6/8/2009	1.50	11.50	2.6E-04
6/8/2009	8.00	4.00	2.4E-04
6/8/2009	7.00	4.50	2.5E-04
6/8/2009	13.50	1.70	2.3E-04

B: = >0.95 ("B" is an indication of saturation)

Max Hydraulic Gradient: = 5

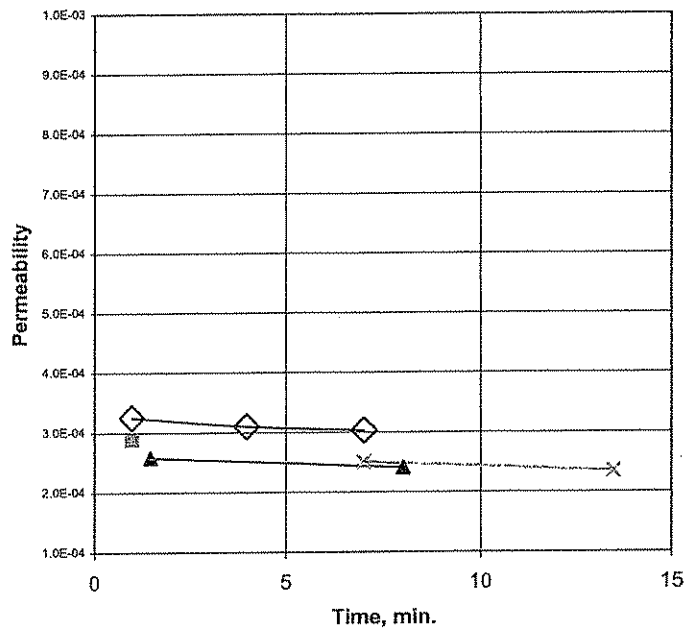

Average Permeability: 3.E-04 cm/sec

Sample Data:	Initial	Final
Height, in	3.00	2.94
Diameter, in	2.38	2.38
Area, in2	4.43	4.43
Volume in3	13.29	13.02
Total Volume, cc	217.8	213.4
Volume Solids, cc	127.4	127.4
Volume Voids, cc	90.4	86.0
Void Ratio	0.7	0.7
Total Porosity, %	41.5	40.3
Air-Filled Porosity, %	15.2	-0.3
Water-Filled Porosity,%	26.3	40.6
Saturation, %	63.5	100.7
Specific Gravity	2.631	2.631
Wet Weight, gm	392.6	421.9
Dry Weight, gm	335.3	335.3
Tare, gm	0.00	0.00
Moisture, %	17.1	25.8
Dry Density, pcf	96.1	98.0

Remarks: Due to slumping of the sample after the confining pressure was released, the final sample dimensions and associated values are approximate.